

ABCs of Spray Finishing

For additional training and troubleshooting information, please visit us online at:

<https://binks.com/troubleshooting/>

Or use this QR code with your mobile device:

TROUBLESHOOTING



For additional copies of this guide, please visit us online at:

<https://binks.com/support/customer-technical-support/>

Or use this QR code with your mobile device:

CUSTOMER/TECHNICAL SUPPORT



Obey local or municipal regulations for product recycling and disposal.

ABOUT THIS MANUAL

ITS PURPOSE

The purpose of this guide is to make information available from many resources on the subject of spray finishing. It is our hope that this guide provides you with a start toward perfecting your finishing skills.

While this guide examines the spray finishing operation and its equipment from many viewpoints, there is still much more to be learned to become truly proficient at spray finishing.

The best way to become proficient at spray finishing is to just do it! Many trade technical and community colleges offer courses in spray finishing which is a great way to improve your skills.

Many of the “tricks” of the professional spray finisher involve paints and coatings. The manufacturers of these materials routinely publish complete books on these subjects. These publications are available in specialty paint stores, as well as, online and will provide you with considerable detail. Many of these books also contain information on techniques for surface preparation.

Another important source of information, particularly on equipment use and selection is your local spray finishing equipment distributor. No guide or website could ever completely cover a specialist’s in-depth knowledge of the equipment, the techniques, the maintenance and troubleshooting.

ITS CONTENTS

This guide has been updated several times from “The ABC’s of Spray Equipment,” originally published by The DeVilbiss Company in 1954. It focuses on equipment and techniques for spray finishing.

This guide is divided into individual sections around the major components of an air spray system...spray guns, electrostatic applicators, material containers, hose, air control equipment, respirators, air compressors, spray booths, pumps, dead end and circulating systems and other sources of information.

A thorough understanding of the material in this guide plus much actual spray painting practice should enable you to handle just about any spray painting situation.

WHO SHOULD USE THIS GUIDE

This guide is intended for all paint users with various levels of knowledge and experience within the paint finishing industry.

MANUAL DISCLAIMER

Although we have made an effort to make this guide as detailed and as complete as possible, be aware that the equipment and product systems used to illustrate points are entirely based on Binks, DeVilbiss and Ransburg technology. DeVilbiss, Ransburg and Binks are three of the world’s oldest and largest manufacturers of spray paint equipment, and have maintained this leadership since its founding in 1888.

This manual was prepared with the most accurate information current at the time of publishing. Binks does not accept responsibility for errors in, or omissions from, the information contained herein.

Please get in touch with your distributor or Binks Customer Service for additional service information and assistance.

TRAINING RELATED MANUALS & PUBLICATIONS

Document Number	Description
77-5300	General Equipment Safety Guide
A28-100R-9	Binks and DeVilbiss Accessories Guide
I-2190	Binks and DeVilbiss Gun Catalog
TL-00-02-R7	Solvent Selection and Cleaning Guide For Electrostatic Equipment

02 CONTENTS

03 GENERAL SAFETY	1-8
SAFETY PRECAUTIONS	1
HAZARDS	2
ADDITIONAL SAFETY INFORMATION	8
04 INTRODUCTION	9-10
FINISHING EQUIPMENT	9
SURFACE PREPARATION.....	9
PAINT PREPARATION.....	9
SOLVENT SELECTION	9
CONTROLLED PAINT RESISTIVITY	9
SOLVENT CLASSIFICATION FOR ELECTROSTATIC USAGE.....	10
VISCOSITY GUIDE.....	10
RESISTANCE ADJUSTMENT BY SOLVENT SELECTION.....	10
EVAPORATION RATES VS. ELECTROSTATIC EQUIPMENT USED.....	10
COATING MATERIAL GUIDE	10
05 AIR ATOMIZING SPRAY GUNS	11-24
INTRODUCTION.....	11
SPRAY GUN TYPES.....	11
OPERATION	17
MAINTENANCE.....	21
TROUBLESHOOTING	23
06 ELECTROSTATIC SPRAY PROCESSES	25-32
PRINCIPLES OF ELECTROSTATICS.....	25
ELECTROSTATIC ADVANTAGES	26
COATING APPLICATION	26
OPERATING ELECTROSTATICS SAFETY	26
ELECTROSTATIC PROCESS & EQUIPMENT	27
ELECTROSTATIC AIR SPRAY ATOMIZATION	27
ELECTROSTATIC HVLP SPRAY ATOMIZATION.....	27
ELECTROSTATIC AIRLESS SPRAY ATOMIZATION.....	27
ELECTROSTATIC AIR ASSISTED AIRLESS ATOMIZATION.....	28
ELECTROSTATIC ELECTRICAL ATOMIZATION.....	28
ELECTROSTATIC ROTARY BELL ATOMIZATION	28
ELECTROSTATIC ROTARY DISK ATOMIZATION.....	28
ELECTROSTATIC POWDER APPLICATION.....	28
OPERATING ELECTROSTATIC COATING SYSTEMS SAFETY: PERSONNEL GROUNDING.....	29
EQUIPMENT GROUNDING	29
GUN GROUNDING	31
NO. 2 APPLICATOR GROUNDING ON SITE PAINTING	31
07 MATERIAL CONTAINERS	33-35
INTRODUCTION	33
08 HOSE AND CONNECTIONS	36-38
INTRODUCTION	36
09 AIR CONTROL EQUIPMENT	39-40
INTRODUCTION	39
10 RESPIRATORS	41-42
INTRODUCTION	41

11 AIR COMPRESSORS	43-44
INTRODUCTION	43
12 SPRAY BOOTHS	45-47
INTRODUCTION	45
13 DIAPHRAGM PUMPS	48-50
INTRODUCTION	48
TROUBLESHOOTING	49
14 HIGH PRESSURE SPRAYING: AIRLESS & AIR ASSISTED AIRLESS	51-52
INTRODUCTION	51
SAFETY	51
AIRLESS AND AIR ASSISTED AIRLESS GUNS	52
15 TWO BALL PISTON PUMPS AND DEAD END SYSTEMS	53-56
INTRODUCTION	53
DEAD END SYSTEMS	54
SYSTEM LAYOUT	55
TROUBLESHOOTING	56
16 FOUR BALL PISTON PUMPS AND CIRCULATING SYSTEMS	57-60
INTRODUCTION	57
CIRCULATING SYSTEMS	58
SYSTEM LAYOUT	59
TROUBLESHOOTING	60
17 APPENDIX	61-64
PAINT AND SOLVENT SPECIFICATIONS	61
VISCOSITY CONVERSION CHART	62
VOLUMETRIC CONTENT OF HOSE OR TUBE (ENGLISH UNITS)	64
VOLUMETRIC CONTENT OF HOSE OR TUBE (METRIC UNITS)	64
18 MANUAL REVISIONS	65
19 CONTACT INFORMATION	67

SAFETY

SAFETY PRECAUTIONS

Before the operation, maintenance, or servicing of this Binks system; fully read and understand all technical and safety literature for your product. This manual contains information that is important for you to know and understand.

This information relates to **USER SAFETY** and the **PREVENTION OF EQUIPMENT PROBLEMS**.

To help you understand this information, we use recognizable ANSI Z535 and ISO warning boxes and symbols throughout this manual. Please obey these safety sections.

⚠ DANGER

DANGER! Indicates a hazardous situation that, if not avoided, will result in death or severe injury.

⚠ WARNING

WARNING! Indicates a hazardous situation that, if not avoided, could result in death or severe injury.

⚠ CAUTION

Caution! Indicates a hazardous situation that, if not avoided, could result in minor or moderate injury, or equipment damage.

NOTICE

Notice: Indicates information considered important but not hazard related.

SAFETY

Safety: Indicates a type of safety instruction, or a separate panel on a safety placard, where specific safety-related instructions or procedures are described.

Careful study and continued use of this manual will provide a better understanding of the equipment functions and procedures.

This understanding will result in improved operation, efficiency, and longer, trouble-free service with faster and easier troubleshooting. If you need the necessary safety literature for your specific system, contact your local Binks representative or Binks directly.

NOTICE

This manual lists standard specifications and service procedures. Differences can occur between this literature and your equipment.

Differences in local or municipal codes, manufacturer or plant requirements, material delivery requirements, and more can make variations unpreventable. To find these differences, compare this manual to your system installation drawings and other applicable Binks equipment manuals.

⚠ WARNING

The user **MUST** read and be familiar with the Safety Section in this manual and the safety literature therein identified.

Only trained personnel can operate this equipment.



All personnel who operate, clean, or maintain this equipment **MUST** fully read and understand this manual! To operate and service the equipment, follow all **WARNINGS** and safety requirements.



The user must be aware of and adhere to **ALL** local building and fire codes and ordinances, as well as **NFPA 33 AND EN 16985 SAFETY STANDARDS, LATEST EDITION**, or applicable country safety standards, before the installation, operation, or servicing of this equipment.





⚠ WARNING

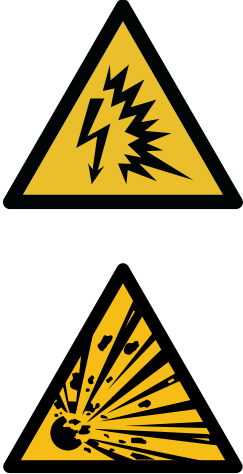

The hazards shown on the pages that follow can occur during the normal use of this Binks equipment, but not all listed hazards will be applicable to your product model or equipment.






Repairs may only be performed by personnel authorized by Binks.


<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Spray Areas</p>  	<p>Fire Hazards</p> <p>Improper or unsatisfactory operation and maintenance procedures will cause a fire hazard.</p> <p>If the safety interlocks are disabled during operation, protection against accidental arcing is shut off and can cause a fire or explosion.</p> <p>Frequent Power Supply or Controller shutdown identifies a problem in the system. For this occurrence, a correction will be necessary</p>	<p>Fire extinguishing equipment must be present in the spray area. Periodically run a test to make sure the equipment stays usable.</p> <p>Keep spray areas clean to prevent the build-up of combustible residues.</p> <p>Do not smoke in the spray area.</p> <p>The high voltage supplied to the atomizer must be turned off before the equipment is cleaned, flushed or maintained.</p> <p>Spray booth ventilation must be kept at the rates as set by NFPA-33, OSHA, country, local, and municipal codes.</p> <p>If flammable or combustible solvents are used to clean the equipment, ventilate the area.</p> <p>Prevent electrostatic arcing. Maintain spark-safe work distance between the parts that get coated and the gun. A span of one inch for every 10KV of the output voltage is necessary.</p> <p>Do an equipment test only in areas free of combustible material. The test may necessitate the high voltage to be on, but only as instructed.</p> <p>Non-factory replacement parts or unauthorized equipment modifications can cause a fire or injury.</p> <p>The key switch bypass is used only during setup operation.</p> <p>Do no production work with disabled safety interlocks.</p> <p>Set up and operate the paint procedure and equipment under NFPA-33, NEC, OSHA, local, municipal, country, and European Health and Safety Norms.</p>

<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Spray Areas</p> 	<p>Explosion Hazard</p> <p>Improper or unsatisfactory operation and maintenance procedures will cause a fire or explosion hazard.</p> <p>If the safety interlocks are disabled during operation, protection against accidental arcing is shut off and can cause a fire or explosion.</p> <p>Frequent Power Supply or Controller shutdown identifies a problem in the system. For this occurrence, a correction will be necessary.</p>	<p>Prevent electrostatic arcing. Maintain spark-safe work distance between the parts that get coated and the gun. A span of one inch for every 10KV of output voltage is necessary.</p> <p>Unless specifically approved for use in hazardous locations, put all electrical equipment outside of Class I or II, Division 1 or 2 hazardous areas in accordance with NFPA-33, or outside of Zone 2 or Zone 22 in accordance with EN standards.</p> <p>If equipped, set the current overload sensitivity as described in the related section of the equipment manual. If incorrectly set, the current overload sensitivity for protection against accidental arcing is turned off and can cause a fire or explosion.</p> <p>Frequent power supply shutdown indicates a problem in the system, which requires correction.</p> <p>Always turn off the control panel power before the system is flushed, cleaned, or servicing the spray system equipment. Make sure no objects are within the spark-safe work distance before the high voltage is turned on.</p> <p>The control panel must interlock with the ventilation system and conveyor in accordance with NFPA-33, EN 50176.</p> <p>Fire extinguishing equipment must be present in the spray area. Periodically run a test to make sure the equipment stays usable. Do an equipment test only in areas free of combustible material.</p>
<p>General Use and Maintenance</p> 	<p>Improper or unsatisfactory operation and maintenance procedures will cause a fire hazard.</p> <p>Personnel must be correctly trained in the operation and maintenance of this equipment.</p>	<p>Train all personnel in accordance with the requirements of NFPA-33, EN 60079-0.</p> <p>Before equipment operation, personnel must read and understand these instructions and safety precautions.</p> <p>Obey appropriate local, municipal, state, and national codes governing ventilation, fire protection, operation maintenance, and housekeeping.</p> <p>Reference OSHA, NFPA-33, EN Norms, and your insurance company requirements.</p>

<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Spray Area High Voltage Equipment</p>    	<p>Electrical Discharge</p> <p>This equipment contains a high-voltage device that can cause an electrostatic induction on ungrounded objects. This electrical charge is capable of igniting coating materials.</p> <p>Insufficient ground will cause a spark hazard. A spark can ignite many coating materials and cause a fire or explosion.</p>	<p>Operators in the spray area and the parts to be sprayed must be sufficiently grounded.</p> <p>All conductive objects inside the spray area must be grounded.</p> <p>Hold the parts that get sprayed on conveyors or hangers that are correctly grounded. The resistance between the parts and the earth-ground must not be more than 1 MΩ. Refer to: NFPA-33.</p> <p>Before the equipment is operated, ground all operators. They cannot wear rubber-soled insulated shoes. Wear ground straps on wrists or legs for sufficient ground contact.</p> <p>Operators must not wear or carry ungrounded metal objects.</p> <p>When used, operators must make complete contact with the gun handle and electrostatic gun. Use conductive gloves or gloves with the palm section cut out.</p> <p>Operators must wear grounded footwear.</p> <p>NOTE: REFER TO NFPA-33 OR SPECIFIC COUNTRY SAFETY CODES FOR GUIDANCE TO CORRECTLY GROUND THE OPERATOR.</p> <p>Except for objects needed for the high-voltage process, all electrically conductive objects in the spray area are to be grounded. Supply a grounded conductive floor in the spray area.</p> <p>Always turn off the gun voltage before the system is flushed, cleaned, or when servicing the spray system equipment.</p> <p>Unless specifically approved for use in hazardous locations, put all electrical equipment outside of Class I or II, Division 1 or 2 hazardous areas in accordance with NFPA-33, or outside of Zone 2 or Zone 22 in accordance with EN standards.</p> <p>Do not install an gun into a fluid system if the solvent supply is ungrounded.</p> <p>Do not touch an energized gun electrode.</p>

<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Spray Areas</p> 	<p>Toxic Fluid or Fumes</p> <p>Toxic fluids or fumes can cause severe injury or death if splashed in the eyes or on the skin, or if inhaled or swallowed.</p>	<p>Read the Safety Data Sheet (SDS) for instructions to know and understand how to handle the specific hazards of the fluids used, and the effects of long-term exposure.</p> <p>During the spray, clean, or servicing of equipment, or when in the work area, keep the work area fully ventilated.</p> <p>Always wear personal protective equipment (PPE) when in the work area or during equipment operation. Refer to the Personal Protective Equipment warnings in this manual.</p> <p>Store hazardous fluid in approved containers and refer to local, municipal, state, and national codes governing the disposal of hazardous fluids.</p>
<p>Spray Area and Equipment Use</p> 	<p>High-pressure fluid sprayed from the gun, hose fittings, or ruptured/damaged components can pierce the skin.</p> <p>While this injury can appear as cut skin, this is a severe injury that can result in the amputation of the affected area.</p>	<p>Do not point or operate the spray gun at the body part of a person.</p> <p>Do not put your hand or fingers over the gun fluid nozzle or fittings in the hose or Proportioner.</p> <p>Do not try to stop or deflect leaks with your hand, glove, body, or shop rag.</p> <p>Do not “blowback” fluid, as the equipment is not an air spray system.</p> <p>Relieve pressure in the supply hoses, Proportioner, and QuickHeat™ hose before the equipment is inspected, cleaned, or serviced.</p> <p>Use the lowest possible pressure to recirculate, purge, or troubleshoot the equipment.</p> <p>Examine the hoses, couplings, and fittings every day.</p> <p>Service or immediately replace parts that leak, are worn, or are damaged. Replace high-pressure hose sections. They cannot be recoupled or serviced.</p>

<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Equipment and Fluids</p> 	<p>Skin and Clothing Burns</p> <p>Equipment surfaces and fluids can become very hot during operation.</p>	<p>Do not touch hot fluid or equipment during operation.</p> <p>Do not let clothing touch the equipment during operation or immediately after the equipment is stopped.</p> <p>Let the equipment fully cool before the examination or servicing of the component.</p>
<p>Pressurized Aluminum Parts</p>    	<p>The use of certain solvents and chemicals can cause equipment damage and severe personal injury.</p>	<p>Do not use 1,1,1-trichloroethane, methylene chloride or other halogenated hydrocarbon solvents or fluids that contain such solvents.</p> <p>These solvents can cause a severe chemical reaction and equipment rupture that results in equipment and property damage, serious bodily injury, or death.</p>

<p>AREAS Indicate possible hazard occurrences.</p>	<p>HAZARDS Indicate possible hazards.</p>	<p>SAFEGUARDS Prevention of possible hazards.</p>
<p>Spray Areas</p> 	<p>Do Not Touch</p> <p>The effect of paint flow rates and formulations on the quality of atomization can cause the turbines to rotate at high speeds.</p>	<p>Do not use a rag or gloved hand against the bell edge to stop or slow down a bell during rotation.</p> <p>Do not try to clean the bell edge during rotation.</p>

⚠ CAUTION

Only operate the equipment after you have read this section.

ADDITIONAL SAFETY INFORMATION

Observe all local or municipal safety measures and wear approved protective equipment when servicing this equipment. Clean all spilled chemicals and materials and do all work in a clean and organized environment to prevent personal injury and equipment damage.

⚠ DANGER

To prevent injury or electrocution while the system is under power, do not contact, disconnect, or manipulate electrical connections or devices. The main disconnect on the right side of the controller can be locked out. Follow the proper Lockout–Tagout (LOTO) procedures for internal controller electrical work.

Only qualified electrical personnel can perform the work if diagnosis and troubleshooting are not possible during working conditions.

⚠ WARNING

To prevent possible chemical spillage when personnel are not on site, air and fluid supplies for the equipment must be disabled when the equipment idles for an extended period, such as an end-of-day shutdown.

NOTICE

During the initial commission of the equipment and at periodic times throughout equipment life, visually examine all fluid fittings for leaks.

Periodically, it is necessary to visually examine all pieces of this equipment for signs of noticeable degradation due to chemicals or other conditions in the equipment's environment.

SAFETY

Obey local or municipal regulations that require installed fire suppression for equipment operation.

If the operation of this equipment, sensors, switches, or other ancillary equipment occurs in the presence of flammable gases and vapors, connect this equipment through intrinsic-safe or Zener barriers. Classify them as a 'simple apparatus' or approve them for use in these areas.

FINISHING EQUIPMENT

This guide is about the selection, use and maintenance of finishing equipment: spray guns, tanks, cups, hoses, compressors, regulators, spray booths, respirators, etc. It presumes that you are familiar with standard surface preparation techniques that may be required before finishing actually begins. It also presumes a basic knowledge of the many different types of paints and coatings available. Creating a perfect finish requires a solid knowledge of surface preparation, finishes and spray painting equipment. The first two are extensively covered in many other books. The manufacturers of paints and coatings have gone to great length to publish information on their new and existing products. But, even an extensive knowledge of surface preparation techniques and paint chemistry is not enough to assure a professional finish. The finish must be applied by a spray gun, and all the variables of its use must be mastered. The equipment necessary to apply the finish – the spray gun, tank, cup, regulator, hoses, compressor, etc. – must all be matched to the job as well as to each other. That equipment must be used and maintained properly, with an appreciation of how and why it works the way it does. The moment of truth for any finish happens when the trigger is pulled. This guide focuses on that moment.

SURFACE PREPARATION

Calibrate the surface to be finished should be well cleaned before painting. If the paint manufacturer's instructions call for it, the surface should be chemically treated. Use a blow-off gun and tack rag to remove all dust and dirt. No amount of primer or paint will cover up a badly prepared surface.

Plastic parts may contain static electricity from the molding process. This static attracts particles of dust and dirt. Eliminate them by treating with "destatisizing" air using a special blow-off gun that imparts a neutral charge to the airflow.

PAINT PREPARATION

Today's finishes are extremely complex chemical formulations. They include both solvent and waterborne types. Some may require the addition of solvents to form the proper spraying viscosity. Others may simply require the addition of a second component at a prescribed ratio to obtain sprayable consistency. Many of them also have hardeners or other chemicals, added to them to insure correct color match, gloss, hardness, drying time or other characteristics necessary to produce a first class finish. Make sure you are familiar with the specific finish material data sheets accompanying each material. Do not mix materials from various manufacturers. Read and follow directions carefully.

All finish materials must also be supplied with Safety Data sheets (SDS). This data provides information on proper handling and disposal of materials. Many states require that SDS be kept on file by the user.

The first step is knowing the type and color of paint the project requires. With these determined, follow the manufacturer's instruction for preparing it exactly. If you have any doubts about how to proceed, don't guess! Contact your paint supplier for help. Improperly prepared paint will never produce a good finish!

The chief characteristic that determines the sprayability of paint and how much film may be applied, is its viscosity or consistency. Following the paint manufacturer's instructions will get you close, but for professional results, use a viscosity cup. It is a simple but very accurate, way to measure the thickness of paint. With the cup, you can thin or reduce the paint to the precise consistency required by the manufacturer.

Always prepare paint in a clean, dust-free environment. Paint has a remarkable ability to pick up dirt. Dirty paint will not only clog your spray gun, but it will also ruin your paint job. Get in the habit of always pouring paint into the cup or tank through a paint strainer. Paint is never as clean as it looks.

SOLVENT SELECTION - ELECTROSTATIC FINISHING

Research engineers have been working for more than thirty years on a continuing development of electrostatic coating processes and equipment, as well as techniques and service to further improve the high efficiency of this process. These techniques can be quite useful for paint formulators by providing better wraparound; higher quality finishes requiring less touch-up and, increasing paint film build. This information is a guide to solvent selection to improve electrostatic sprayability.

CONTROLLED PAINT RESISTIVITY - A FACTOR IN FORMULATION

It has been determined that coating formulations for electrostatic application, in addition to meeting customer requirements for durability, drying time, gloss, etc., should have an electrical resistance within a specified range for best atomizing characteristics and electrical deposition. Electrical resistivity is a characteristic which must be built into the paint formulation. It has generally been found that most materials can be adjusted to have suitable resistance and still meet other requirements. We have found that no single, simple characteristic or adjustment provides optimum sprayability for any given coating. However, adjustment of paint resistivity through appropriate selection of solvents improves many paints that otherwise could not be sprayed efficiently by the electrostatic process.

SOLVENT CLASSIFICATION FOR ELECTROSTATIC USAGE

Solvents may be classified as polar or nonpolar. For our purposes, the differences in polarity between different solvents provides a means to adjust the total resistivity of a paint mixture. Nonpolar solvents normally do not improve sprayability. These solvents include the aliphatic and aromatic hydrocarbons, chlorinated solvents, and the turpentine. The addition of polar solvents compatible with the basic coating material often improves electrostatic sprayability. Polar solvents include the ketones, alcohols, glycol ethers, esters, and nitroparaffins.

VISCOSITY GUIDE

The initial trial paint formulation should be of high viscosity (preferably exceeding 50 seconds on a No. 4 Ford cup) so that the reduced formula will have satisfactorily high solids content after solvent additions. It is usually best to adjust viscosity after resistivity, since viscosity is a less critical factor for electrostatic sprayability.

RESISTANCE ADJUSTMENT BY SOLVENT SELECTION

Nonpolar solvents may be used as extenders to vary paint viscosity or flow properties without seriously changing the electrical resistance of the mixture. An exception occurs with paints that are of low resistivity, for example vinyl solutions or nitrocellulose materials. The conductivity of these special mixtures may sometimes be reduced to a usable factor by the addition of nonpolar solvents.

Generally, the additions of solvent of highest polarity will give the greatest electrical resistance reduction to a mixture' solvents of intermediate polarity provide intermediate resistance reductions, etc. The adjustment of paint resistivity to the specified optimum ranges will usually improve its sprayability. A specific selection should be based on the best compromise to obtain the desired resistivity, viscosity, flow rate, evaporation rate, cost, and other conventionally considered factors.

NOTICE

Please see the Appendix section for further details on solvent selection, evaporation rates and guide to measuring viscosity.

EVAPORATION RATES VS. ELECTROSTATIC EQUIPMENT USED

All Ransburg No. 2 Process disk equipment requires slower formulations than normally used for conventional hand air guns. The larger disk diameter and higher the speed of rotation, the slower the evaporation rates should be made. No. 2 Process bells require paints in about the same evaporation range as for conventional air guns, while the No. 2 Process handguns require still faster solvents. Because of complex interactions of solvents, resins, and binders, it may happen that a solvent of a certain polarity will reduce the mixture resistance more than an equal amount of a second solvent which has a higher polarity. As these reactions are not always predictable, the adjustment of resistivity is necessarily a guide trial-and-error procedure.

COATING MATERIAL GUIDE

Short oil length alkyd vehicles, with small amounts of high polarity modifying resins like amino resins, epoxy, or phenolic, respond well to the adjustment of resistivity by solvent addition.

Air-dry lacquers and similar fast drying materials usually contain so much polar solvent that their resistivity is below the desired range. In such cases, incorporating the maximum allowable quantity of nonpolar dilutant (example: the substitution of esters for ketones) will improve sprayability.

Organosols dispersed in hydrocarbons can be improved by thinning just before use with the polar solvents of high solvency. Reduction long before use with polar solvents of low solvency and swellability for the dispersed resin is also beneficial.

Most paints of high pigment volume concentration and paints where the binder is highly nonpolar, such as bodied linseed oil, styrenated alkyds, lacquers based on hydrocarbon resins (like cyclized rubber or butylene copolymers), and long oil alkyds, may be improved by solvent adjustment, but the possible upgrading of these materials by this method is limited. Preliminary Ransburg research seems to indicate that the use of concentrated additives with paints of these types offers a better prospect for sprayability improvement.

INTRODUCTION

The spray gun is the key component in a finishing system. It is a precision engineered and manufactured instrument. Each type and size is specifically designed to perform a certain, defined range of tasks.

As in most other areas of finishing work, having the right tool for the job goes a long way toward getting professional results.

This chapter will help you know which is the proper gun by reviewing the Conventional Air, LVMP (Trans-Tech) and High Volume/Low Pressure (HVLP) spray gun designs commonly used in finishing—siphon feed, gravity feed and pressure feed. It will also review the different types of guns and components within each design.

A thorough understanding of the differences between systems will allow you to select the right gun, to use it properly to produce a high quality finish and to contribute toward a profitable finishing operation.

SPRAY GUN TYPES

1. WHAT IS AN AIR ATOMIZING SPRAY GUNS?

Air atomizing spray guns are available in three types: Conventional, Low Volume Medium Pressure (LVMP) (Trans-Tech) and High Volume Low Pressure (HVLP).

Conventional air spray guns pass virtually all the input pressure to the air cap. HVLP reduces the air pressure internally to a much lower pressure (10 psi atomizing pressure). LVMP is higher pressures than HVLP but substantially lower than conventional. LVMP is nearly as efficient as HVLP but will render a finish much closer to conventional.

Air and material enter the spray gun through separate passages, and are mixed at the air cap in a controlled pattern.

2. WHAT ARE THE TYPES OF AIR SPRAY GUNS?

Air spray guns may be classified in various ways. One way is by the location of the material container:

Figure 1 shows a gun with a cup attached below it.

Figure 3 shows a gun with a cup attached above it.

Figure 4 shows a material container some distance away from its pressure feed gun.

The type of material feed system is also a way of classifying guns:

Siphon Feed: draws material to the gun by siphoning as in Figure 1.

Gravity Feed: the material travels down, carried by its own weight and gravity as in Figure 3.

Pressure Feed: the material is fed by positive pressure as in Figure 4.

Guns may also be classified as either external or internal mix.

3. WHAT IS A SIPHON FEED GUN?

A spray gun design in which a stream of compressed air creates a vacuum at the air cap, providing a siphoning action. Atmospheric pressure on the material in the siphon cup forces it up the pickup tube, into the gun and out the fluid tip, where it is atomized by the air cap. The vent holes in the cup lid must be open. This type gun is usually limited to a one-quart, or smaller, capacity container.



Figure 1: Siphon Feed Gun With Attached Cup

Siphon feed is easily identified by the fluid tip extending slightly beyond the face of the air cap, as shown in Figure 2.

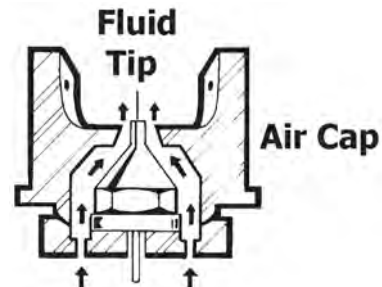


Figure 2: Siphon Feed Air Cap

Siphon feed guns are suited to many color changes and to small amounts of material, such as in touchup or lower production operations.

4. WHAT IS A GRAVITY FEED GUN?

This design uses gravity to flow the material from the cup, which is mounted above the gun, into the gun for spraying. No fluid pickup tube is used, since the fluid outlet is at the bottom of the cup.

This cup has a vent hole at the top of the cup which must remain open. It is limited to 32 ounce capacities due to weight and balance.

Gravity feed guns are ideal for small applications such as spot repair, detail finishing or for finishing in a limited space. They require less air than a siphon feed gun, and usually have less overspray.



Figure 3: Gravity Feed Gun With Attached Cup

This system is normally used when large quantities of material are to be applied, when the material is too heavy to be siphoned from a container or when fast application is required. Production spraying in a manufacturing plant is a typical use of a pressure feed system

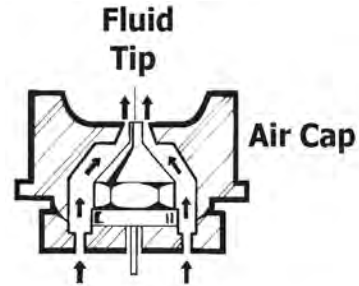


Figure 5: Pressure Feed Air Cap

NOTICE

When using a gravity feed system, downsize the tip one size from siphon. If the siphon system calls for a .070", use a .055 or .062".

5. WHAT IS A PRESSURE FEED GUN?

In this design, the fluid tip is flush with the face of the air cap (see Figure 5). The material is pressurized in a separate cup, tank or pump. The air pressure forces the material through the fluid tip and to the air cap for atomization.

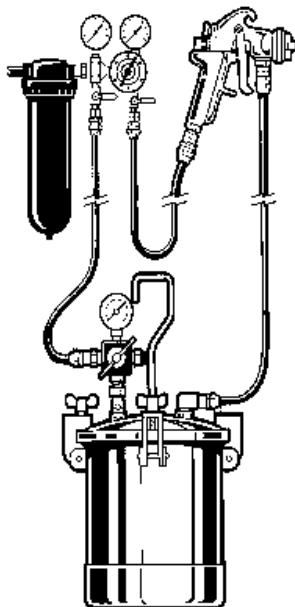


Figure 4: Typical Pressure Feed Gun With Remote Tank

Table 1: Atomization Technology Comparison

Feed Type	Viscosity (#2 Zahn)	Fluid (OZ/Minute)	Atomizing Pressure	Production Type
Siphon	Up to 24	10-12	40-50	Low
Gravity	Up to 24	10-12	30-40	Low
Pressure	Up to 29	20-24	50-60	High
HVLP	Up to 29	14-16	10	High

6. WHAT IS AN EXTERNAL MIX GUN?

This gun mixes and atomizes air and fluid outside the air cap. It can be used for applying all types of materials, and it is particularly desirable when spraying fast drying paints such as lacquer. It is also used when a higher quality finish is desired.

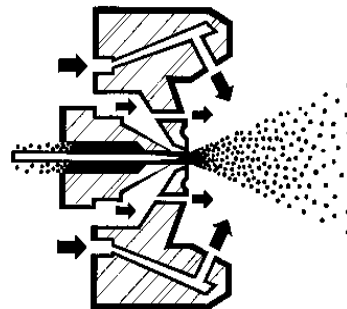


Figure 6: External Mix Gun

7. WHAT IS AN INTERNAL MIX GUN?

This gun mixes air and material inside the air cap, before expelling them. It is usually used where low air pressures and volumes are available, or where slow drying materials are being sprayed. A typical example is spraying flat wall paint, or outside house paint, with a small compressor. Internal mix guns are rarely used for finishing when a fast-drying material is being sprayed, or when a high quality finish is required.

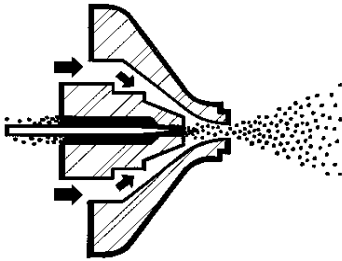


Figure 7: Internal Mix Gun

8. WHAT IS HVLP?

HVLP, or High-Volume/Low Pressure, uses a high volume of air (typically between 15-26 CFM) delivered at low pressure (10 psi or less at the air cap) to atomize paint into a soft, low-velocity pattern of particles. In most cases, less than 10 psi is needed in order to atomize.

Proper setup utilizes no more fluid and air pressure than is needed to produce the required quality and a flow rate that will meet production requirements. As a result, far less material is lost in over spray, bounce back and blow back than with conventional air spray. This is why HVLP delivers a dramatically higher transfer efficiency (the amount of solids applied as a percent of solids sprayed) than spray systems using a higher atomizing pressure.

The HVLP spray gun resembles a standard spray gun in shape and operation. Models that use high inlet pressure (20-80 psi) and convert to low pressure internally within the spray gun are called HVLP conversion guns. Some HVLP models, particularly those using turbines to generate air, bleed air continuously to minimize back pressure against the air flow of the turbine. The air cap design is similar to that of a standard spray gun, with a variety of air jets directing the atomizing air into the fluid stream, atomizing it as it leaves the tip.

HVLP is growing in popularity and new environmental regulations are requiring it for many applications. HVLP can be used with any low-to-medium solids materials that can be atomized by the gun, including two-component paints, urethanes, acrylics, epoxies, enamels, lacquers, stains, primers, etc.

9. WHAT ARE THE PRINCIPAL PARTS OF A SPRAY GUN?

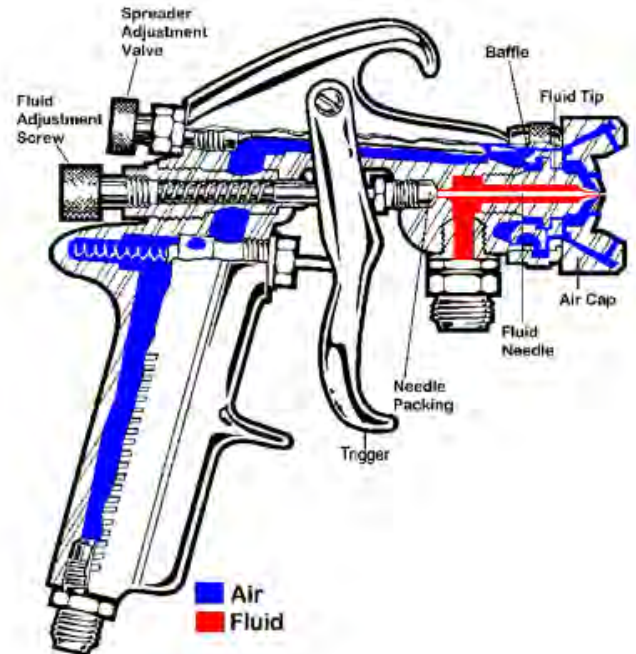


Figure 8: The Anatomy Of A Spray Gun

10. WHAT HAPPENS WHEN THE TRIGGER IS PULLED?

The trigger operates in two stages. Initial trigger movement opens the air valve, allowing atomizing air to flow through the gun.

Further movement of the trigger opens the fluid needle, allowing fluid material to flow. When the trigger is released, the fluid flow stops before the atomizing air flow.

This lead/lag time in the trigger operation, assures a full spray pattern when the fluid flow starts. It also assures a full pattern until the fluid flow stops, so there is no coarse atomization.

11. WHAT IS THE FUNCTION OF THE AIR CAP?

The air cap (see Figure 10) directs compressed air into the fluid stream to atomize it and form the spray pattern. (see Figure 9)

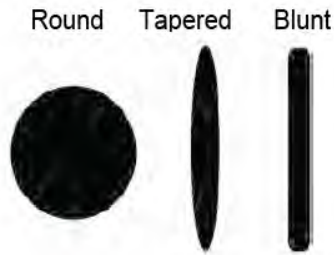


Figure 9: Types Of Spray Patterns

There are various styles of caps to produce different sizes and shapes of patterns for many applications.

12. WHAT ARE THE ADVANTAGES OF THE MULTIPLE JET CAP?

This cap design provides better atomization of more viscous materials. It allows higher atomization pressures to be used on more viscous materials with less danger of split spray pattern. It provides greater uniformity in pattern due to better equalization of air volume and pressure from the cap. It also provides better atomization for materials that can be sprayed with lower pressures.

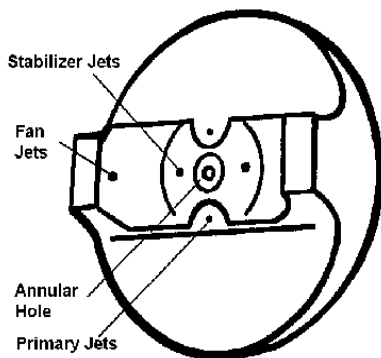


Figure 10: External Mix Air Cap

13. HOW SHOULD AN AIR CAP BE SELECTED?

The following factors must be considered:

- Type, viscosity and volume of material to be sprayed
- Size and nature of object, or surface, to be sprayed

NOTICE

Multiple, or larger, orifices increase ability to atomize more material for faster painting of large objects.

Fewer, or smaller, orifices usually require less air, produce smaller spray patterns and deliver less material. These caps are designed for painting smaller objects and/or using slower speeds.

c) Material feed system used - pressure, siphon or gravity

d) Size of fluid tip to be used (Most air caps work best with certain fluid tip/needle combinations.)

e) Volume of air in cubic feet per minute (cfm) and pressure in pounds per square inch (psi) available

See your specific gun service manual for the proper selection of air cap, fluid tip and needle combinations based upon your qualifications.

14. WHAT IS THE FUNCTION OF THE FLUID TIP AND NEEDLE?

They restrict and direct the flow of material from the gun into the air stream. The fluid tip forms an internal seat for the tapered fluid needle, which reduces the flow of material as it closes. (see Figure 11)

The amount of material that leaves the front of the gun depends upon the viscosity of the material, the material fluid pressure and the size of the fluid tip opening provided when the needle is unseated from the tip. Fluid tips are available in a variety of sizes to properly handle materials of various types, flow rates and viscosities.

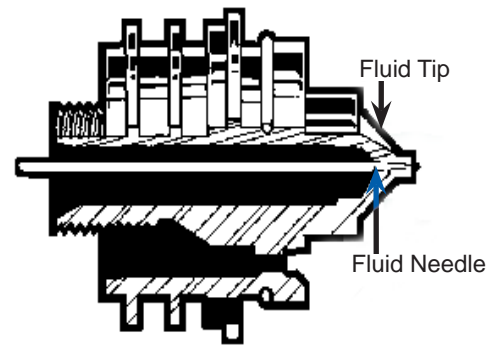


Figure 11: The Fluid Tip And Needle

15. WHAT IS THE NOZZLE COMBINATION?

In practice, the air cap, fluid tip, needle and baffle are selected as a unit, since they all work together to produce the quality of the spray pattern and finish. These four items, as a unit, are referred to as the nozzle combination.

16. WHAT ARE THE STANDARD FLUID TIP SIZES AND FLOW RATES?

The standard sizes, corresponding fluid tip opening dimensions and flow rates are:

Table 2: Conventional Air Spray	
Fluid Tip I.D.	Flow Rate / Material
Pressure Feed Systems	
.028"/.7mm	Up to 12 oz/min
.0425"/1.1mm	Up to 20 oz/min
.055"/1.4mm	Up to 30 oz/min
.070"/1.8mm	Over 30 oz/min
.070"/1.8mm	Porcelain enamel
.086"/2.2mm	Heavy body materials
.110"/2.75mm	Heavy body materials
Siphon Feed Systems	
.070"/1.8mm	Up to 12 oz/min
.062"/1.6mm	Up to 10 oz/min
Gravity Feed Systems	
.055"/1.4mm	Up to 30 oz/min
.062"/1.6mm	Up to 30 oz/min

Table 3: HVLP / LVMP	
Fluid Tip I.D.	Flow Rate / Material
Pressure Feed Systems	
.0425"/1.1mm	Up to 10 oz/min
.055"/1.4mm	Up to 14 oz/min
.070"/1.8mm	Up to 20 oz/min
.086"/2.2mm	Over 20 oz/min
Siphon Feed Systems	
.086"/2.2mm	Up to 9 oz/min
.070"/1.8mm	Up to 8 oz/min
Gravity Feed Systems	
.055"/1.4mm	Up to 12 oz/min
.062"/1.6mm	Up to 12 oz/min

NOTICE

Optimum fluid pressures are 8-20 psi. Pressures greater than this generally indicate the need for a larger fluid tip size.

17. HOW ARE FLUID TIP AND NEEDLE SIZES IDENTIFIED?

DeVilbiss and Binks fluid tips and needles are identified by the letters or numbers stamped on the tip and the needle. The identification letters on these components should match. See the appropriate DeVilbiss/Binks spray gun guide for the proper selection of fluid tip and needle combinations.

18. WHAT FLUID TIP AND NEEDLE COMBINATION SIZES ARE MOST COMMON?

.042/1.1mm, .055/1.4mm and .070/1.8mm are most commonly used. The .070/1.8mm size is used for siphon feed, while .055/1.4mm and .062/1/6 are used for gravity Feed. For pressure feed the most common tips are .042/1.1mm, .055/1.4mm and .070/1.8mm.

19. HOW ARE NOZZLE COMBINATIONS SELECTED?

Five basic considerations are involved in selecting the nozzle combination:

- type and viscosity of material being sprayed.
- physical size of object being finished.
- desired speed/finish quality.
- gun model being used.
- available air volume (cfm) and pressure (psi) from compressor.

The type and viscosity of the material being sprayed is the first factor to consider.

NOTICE

The lower the viscosity of the material, the smaller the I.D. of the fluid tip.

Table 4: Pressure Feed

Material Viscosity (#2 Zahn)	Flow Rate	Tip Size
Up to 23 sec	Low	.0425"/1.1mm
23-28 sec	Medium	.055"/1.4mm
28-48 sec	High	.070"/1.8mm
Over 48 sec	High	.086"/2.2mm

NOTICE

Viscosity conversion charts are available to convert one viscosity cup reading to another from any material or equipment supplier.

The physical size of the object to be painted must also be considered. As a general rule, use the largest possible spray pattern consistent with the object size. Remember that different air caps deliver various pattern characteristics. This can reduce both spraying time and the number of gun passes.

The next consideration in evaluating nozzle combinations is the speed with which the finish will be applied, and the desired level of quality. For speed and uniform coverage, choose a nozzle combination which produces a pattern as wide as possible.

For finish coat work, quality is the deciding factor. Choose a nozzle combination which produces a fine atomization and a smaller pattern size, thereby giving greater application control.

The model of the gun itself will limit the selection of nozzle combination. For a siphon feed gun, there are two nozzle types available which are suitable for finishing operations. These nozzles have fluid tip openings of .070"/1.8mm to .086"/2.2mm, and are designed to handle viscosities up to 28 seconds in a No. 2 Zahn Viscosity Cup.

For a pressure feed gun, the amount of material discharged depends upon material viscosity, the inside diameter of the fluid tip, the length and size of hose and the pressure on the material container or pump.

If the fluid tip opening is too small, the paint stream will be too high. If the fluid tip opening is too large, you will lose control over the material discharging from the gun.

For most HVLP guns, the paint flow shouldn't exceed 16 oz. per minute. For recommended flow rates for each fluid tip size, consult the DeVilbiss or Binks guide.

Lastly, available air supply is the last factor to consider. Pressure feed air caps consume between 7.0 and 26.0 CFM, depending on air pressure applied. If your air supply is limited, because of an undersized compressor, or many other air tools are in use at once, the gun will be starved for air, producing incomplete atomization and a poor finish.

20. WHAT ARE THE CRITERIA FOR SELECTING A PRESSURE FEED NOZZLE?

While the fluid discharge in ounces per minute from a siphon feed gun is relatively stable (largely because it is determined by atmospheric pressure), the fluid discharge from a pressure feed gun depends more upon the size of the inside diameter of the fluid tip and the pressure on the paint container or pump. The larger the opening, the more fluid is discharged at a given pressure.

If the fluid tip ID is too small for the amount of material flowing from the gun, the discharge velocity will be too high. The air, coming from the air cap, will not be able to atomize it properly causing a center-heavy pattern.

If the fluid tip opening is too large, material discharge

control will be lost, often resulting in a split pattern.

The fluid tip/air cap combination must be matched to each other and to the job at hand. Spray gun catalogs include charts to help you match them properly.

21. OF WHAT METALS ARE THE FLUID TIPS MADE?

Tips are made of the following metals:

- 300-400 grade stainless steel for both non-corrosive and corrosive materials
- Carboly inserts for extremely abrasive materials

22. WHAT IS VISCOSITY?

The viscosity of a liquid is its body, or thickness, and it is a measure of its internal resistance to flow. Viscosity varies with the type and temperature of the liquid. Any reference to a specific viscosity measurement must be accompanied by a corresponding temperature specification.

Viscosity is usually measured in poise and centipoise (1 poise=100 centipoise). The most common measurement used to determine viscosity in finishing is flow rate (measured in seconds from a Zahn, Ford or Fisher Viscosity Cup).

Viscosity conversion may be accomplished by consulting a viscosity conversion chart.

Different viscosity cup sizes are used for different thicknesses of materials. Each cup has a precision hole at the bottom of the cup. Use a smaller or larger hole in the cup depending on the thickness of the material.

Viscosity control is an extremely important and effective method to maintain application efficiency and quality consistency. Always measure viscosity after each batch of material is mixed and make sure material temperature is the same, normally 70° to 90° F.

Consult your coatings Technical Data Sheet for temperature commendations.

23. WHAT IS THE SPREADER ADJUSTMENT VALVE?

A valve for controlling the air to the horn holes which regulate the spray pattern from maximum width down to a narrow or round pattern. (See Figure 8)

24. WHAT IS THE FLUID NEEDLE ADJUSTMENT?

This adjustment controls the travel of the fluid needle, which allows more or less material through the fluid tip.

See Figure 8.

With pressure feed systems, the fluid delivery rate should be adjusted by varying the fluid pressure at the pressure pot. Use the fluid adjustment knob for minor and/or temporary flow control. This will extend the life of the fluid needle and tip.

25. WHAT ARE THE COMPONENTS OF SIPHON AND GRAVITY FEED SYSTEMS?

Typical siphon and gravity feed systems consist of; a siphon feed or gravity feed spray gun with cup, an air compressor (not shown), a combination filter/air regulator and air hoses. (See Figure 12)

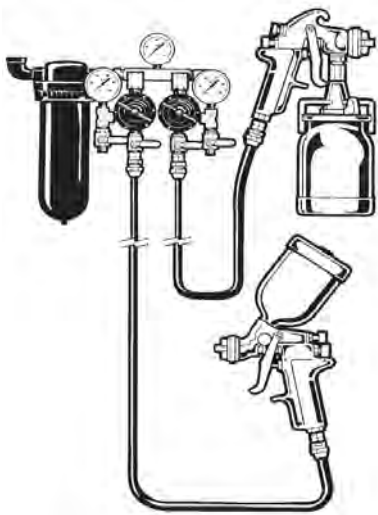


Figure 12: Siphon Feed And Gravity Feed System Components

OPERATION

26. HOW IS SIPHON AND GRAVITY FEED EQUIPMENT HOOKED UP FOR OPERATION?

Connect the air supply from the compressor outlet to the filter/air regulator inlet.

Connect the air supply hose from the air regulator outlet to the air inlet on the spray gun.

After the material has been reduced to proper consistency, thoroughly mixed and strained, pour it into the cup and attach the cup (siphon feed) or attach the cup and fill with the coating (gravity feed).

27. HOW ARE SIPHON AND GRAVITY FEED SYSTEMS INITIALLY ADJUSTED FOR SPRAYING?

1. Spray a horizontal test pattern (air cap horns in a vertical position). Hold the trigger open until the paint begins to run. There should be even distribution of the paint across the full width of the pattern. (see Figure 13). The fan control knob is normally adjusted fully counter-clockwise. If the distribution is not even but is symmetrical a different fluid tip may help. If the pattern is not symmetrical, there is a problem with either the air cap or the fluid tip/needle that must be corrected.

Refer to the Troubleshooting Section for examples of faulty patterns to help diagnose your problem.

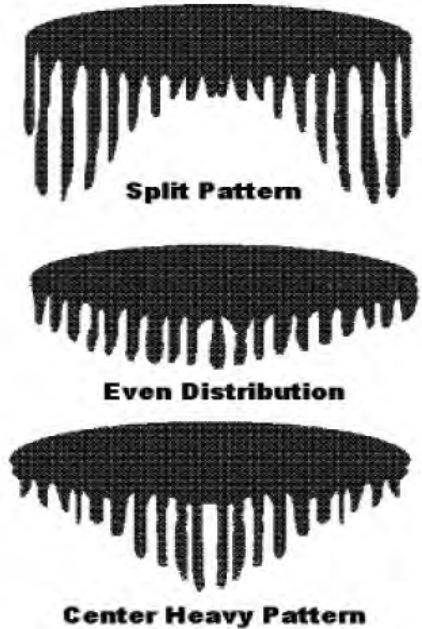


Figure 13: Horizontal Test Pattern

2. Flush If the pattern produced by the above test appears normal, rotate the air cap back to a normal spraying position and begin spraying. (Example - a normal pattern with a #30 air cap will be about 9" long when the gun is held 8" from the surface).



Figure 14: Fluid Adjustment Screw

3. With the fluid adjusting screw open to the first thread, and the air pressure set at approximately 30 psi, make a few test passes with the gun on some clean paper. If there are variations in particle size, specks and/or large globs, the paint is not atomizing properly (see Figure 19).

- If the paint is not atomizing properly, increase the air pressure slightly and make another test pass. Continue this sequence until the paint particle size is uniform.

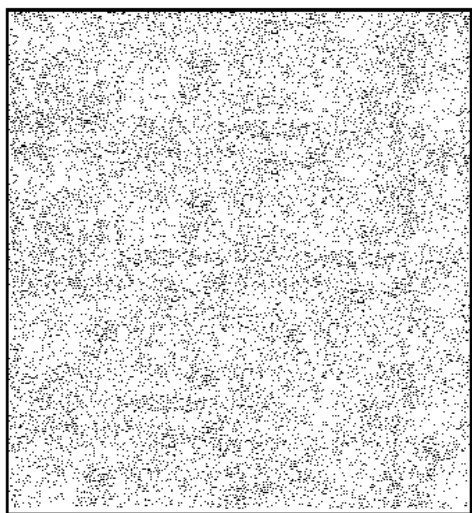
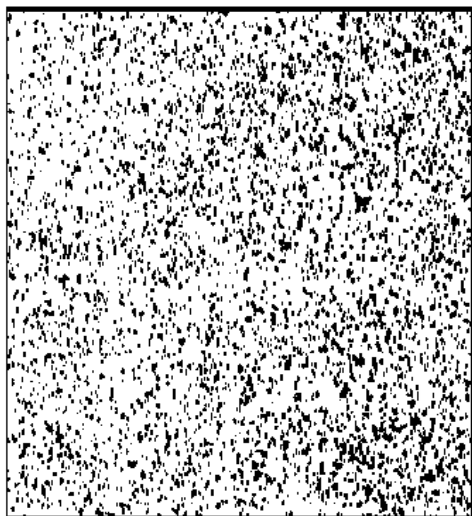


Figure 15: Test Patterns

- If the pattern seems starved for material, and the fluid adjusting screw is open wide (to the first thread), the atomization air pressure may be too high, or the material may be too heavy. Recheck the viscosity or reduce the air pressure.

- If the material is spraying too heavily and sagging, reduce the material flow by turning in the fluid adjusting screw (clockwise). Remember, proper setup utilizes no more fluid and air pressure than is needed to produce the required quality and a flow rate that will meet production requirements.

28. WHAT ARE THE COMPONENTS OF A PRESSURE FEED SYSTEM?

A pressure feed system consists of; a pressure feed spray gun, a pressure feed tank, cup or pump, an air filter/regulator, appropriate air and fluid hoses and an air compressor. See Figure 16

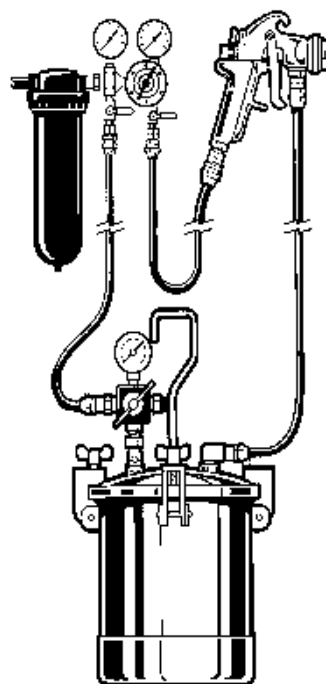


Figure 16: Pressure Feed System Components

29. HOW IS EQUIPMENT HOOKED UP FOR PRESSURE FEED SPRAYING?

Connect the air hose from the air regulator to the air inlet on the gun. Connect the mainline air hose to the air inlet on the tank, cup or pump.

⚠ CAUTION

Do not exceed the container's maximum working pressure.

Connect the fluid hose from the fluid outlet on the tank to the fluid inlet on the gun.

30. HOW IS THE PRESSURE FEED GUN ADJUSTED FOR SPRAYING?

Open spreader adjustment valve for maximum pattern size. (see figure 8) Open fluid adjustment screw (counter clockwise) until maximum needle travel is achieved. Opening beyond that point will lessen the internal spring tension and leakage at the fluid tip may result.

31. HOW IS THE PRESSURE FEED GUN BALANCED FOR SPRAYING?

1. Using control knob on fluid regulator, set fluid pressure at 5 to 10 psi.
2. Using control knob on air regulator, set air atomization pressure at 30-35 psi.
3. Spray a test pattern (fast pass) on a piece of paper, cardboard, or wood. From that test pattern, determine if the particle size is small enough and uniform throughout the pattern to achieve the required finish quality. If particle size is too large or is giving too much texture in the finish, turn the atomization pressure up in 3 to 5 psi increments until particle size and texture of finish is acceptable.
4. Spray a part with these settings. If you are not able to keep up with the production rate required or if the finish is starved for material, increase the fluid pressure (or use a larger capacity fluid tip) with the fluid regulator control knob in 2 to 4 psi increments until required wet coverage is accomplished.
5. Remember, as you turn up the fluid pressure the particle size will increase. Once the coverage required is obtained, it will be necessary to re-adjust the atomization pressure in 3 to 5 psi increments as explained in step 3 to insure required particle size and finish texture is achieved.

6. If using HVLP, using an "Air Cap Test Kit", verify that the air cap pressure is not above 10 psi if required by a regulatory agency.

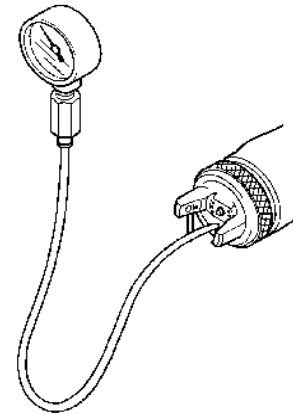


Figure 17: Air Cap Test Kit

After establishing the operating pressures required for production and finish quality, develop a Pressure Standardization program for your finish room to follow.

32. WHAT IS A PRESSURE STANDARDIZATION PROGRAM?

After establishing air and fluid pressures that meet required quality and production, record the data to be used for that application for future reference. (see figure 18)

Booth # _____
Material Sprayed _____
Application _____
Viscosity _____
Fluid Temperature _____
Spray Gun Model _____
Air Cap _____ Fluid Tip _____
Air Pressure _____
Fluid Pressure _____

Figure 18: Pressure Standardization Chart

33. HOW SHOULD THE SPRAY GUN BE HELD?

It should be held so the pattern is perpendicular to the surface at all times. Keep the gun tip 8-10 inches (air spray guns) or 6-8 inches (HVLP guns) from the surface being sprayed.

34. WHAT IS THE PROPER TECHNIQUE FOR SPRAY GUN STROKE AND TRIGGERING?


The stroke is made with a free arm motion, keeping the gun at a right angle to the surface at all points of the stroke. Triggering should begin just before the edge of the surface to be sprayed is in line with the gun nozzle. The trigger should be held fully depressed, and the gun moved in one continuous motion, until the other edge of the object is reached. The trigger is then released, shutting off the fluid flow, but the motion is continued for a few inches until it is reversed for the return stroke.

When the edge of the sprayed object is reached on the return stroke, the trigger is again fully depressed and the motion continued across the object. Lap each stroke 50% over the preceding one. Less than 50% overlap will result in streaks on the finished surface. Move the gun at a constant speed while the trigger is pulled, since the material flows at a constant rate.


Another technique of triggering is referred to as "feathering." Feathering allows the operator to limit fluid flow by applying only partial trigger travel.

35. WHAT HAPPENS WHEN THE GUN IS ARCED?

Arcing the stroke results in uneven application and excessive overspray at each end of the stroke. When the tip is arced at an angle 45 degrees from the surface (see figure 19), approximately 65% of the sprayed material is lost.

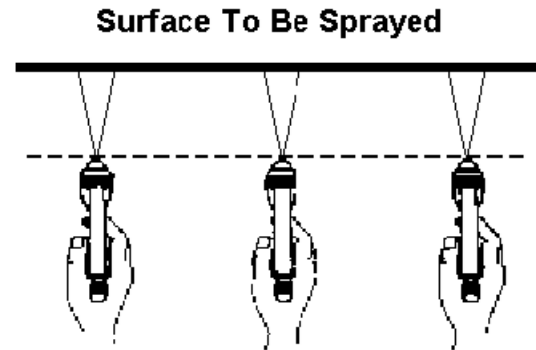

- **Wrist Flexible**
- **Gun Travels Straight**
- **Even Coating**
- **Correct**

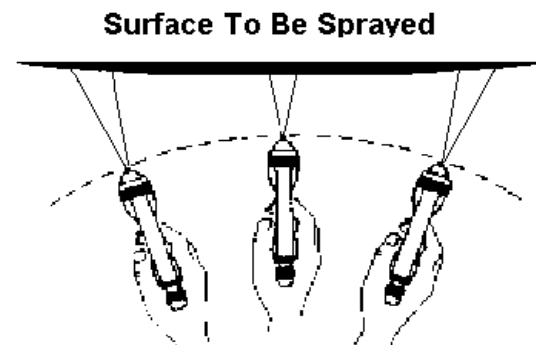

- **Wrist Not Flexible**
- **Arching Gun**
- **Uneven Coating**
- **Incorrect**

Figure 19: Spray Techniques

36. WHAT IS THE PROPER SPRAYING SEQUENCE AND TECHNIQUE FOR FINISHING APPLICATIONS?

Difficult areas, such as corners and edges, should be sprayed first. Aim directly at the area so that half of the spray covers each side of the edge or corner. Hold the gun an inch or two closer than normal, or screw the spreader adjustment control in a few turns. Needle travel should be only partial by utilizing the "feathering" technique. Either technique will reduce the pattern size.

If the gun is just held closer, the stroke will have to be faster to compensate for a normal amount of material being applied to smaller areas. When spraying a curved surface, keep the gun at a right angle to that surface at all times. Follow the curve. While not always physically possible, this is the ideal technique to produce a better, more uniform, finish.

After the edges, flanges and corners have been sprayed, the flat, or nearly flat, surfaces should be sprayed. Remember to overlap the previously sprayed areas by 50% to avoid streaking. When painting very narrow surfaces, you can switch to a smaller gun, or cap with a smaller spray pattern, to avoid readjusting the full size gun. The smaller guns are usually easier to handle in restricted areas. A full size gun could be used, however, by reducing the air pressure and fluid delivery and triggering properly.

MAINTENANCE

37. HOW SHOULD THE AIR CAP BE CLEANED?

Remove the air cap from the gun and immerse it in clean solvent. Blow it dry with compressed air. If the small holes become clogged, soak the cap in clean solvent. If reaming the holes is necessary, use a toothpick, a broom straw, or some other soft implement. (see figure 20) Cleaning holes with a wire, a nail or a similar hard object could permanently damage the cap by enlarging the jets, resulting in a defective spray pattern.



Figure 20: Cleaning The Air Cap

38. HOW SHOULD GUNS BE CLEANED?

A siphon or pressure feed gun with attached cup should be cleaned as follows:

Turn off the air to the gun, loosen the cup cover and remove the fluid tube from the paint. Holding the tube over the cup, pull the trigger to allow the paint to drain back into the cup.

Empty the cup and wash it with clean solvent and a clean cloth. Fill it halfway with clean solvent and spray it through the gun to flush out the fluid passages by directing stream into an approved, closed container.

SAFETY

All containers used to transfer flammable materials should be grounded. Be sure to comply with local codes regarding solvent disposal.

Then, remove the air cap, clean it as previously explained and replace it on the gun. Wipe off the gun with a solvent soaked rag, or if necessary, brush the air cap and gun with a fiber brush using clean-up liquid or thinner.

To clean a pressure feed gun with remote cup or tank, turn off air supply to cup or tank. Release material pressure from the system by opening relief valve.

Material in hoses may be blown back. Lid must be loose and all air pressure off. Keep gun higher than container, loosen air cap and trigger gun until atomizing air forces all material back into the pressure vessel.

A gun cleaner may be used for either type of gun. This is an enclosed box-like structure (vented) with an array of cleaning nozzles inside.

Guns and cups are placed over the nozzles, the lid is closed, the valve is energized, and the pneumatically controlled solvent sprays through the nozzles to clean the equipment.

SAFETY

The solvent is contained, and must be disposed of properly.

NOTICE

Some states codes require the use of a gun cleaner, and it is unlawful to discharge solvent into the atmosphere.

After cleaning a spray gun in a gun cleaner, be sure to lubricate as indicated in Figure 22.

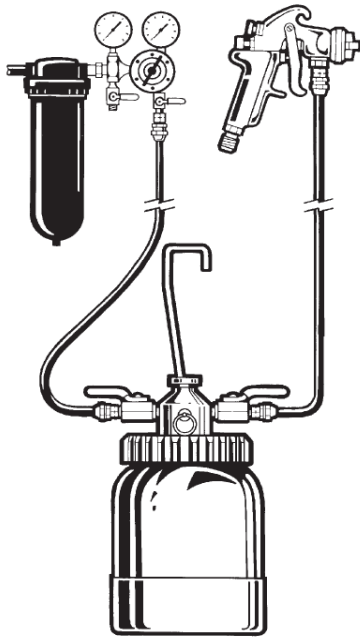


Figure 21: Using A Hose Cleaner

Use a hose cleaner to clean internal passages of spray guns and fluid hose. This device incorporates a highly efficient fluid header, which meters a precise solvent/air mixture. The cleaner operates with compressed air and sends a finely atomized blast of solvent through the fluid passages of the hose, the spray gun, etc. This simple, easy to use cleaner speeds up equipment cleaning and saves solvent. Savings may be as much as 80%. It also reduces VOC emissions.

SAFETY

Be sure that both the hose cleaner and gun are properly grounded.

NOTICE

Where local codes prohibit the use of a hose cleaner, manually backflush the hose into the cup or tank with solvent and dry with compressed air.

Clean the container and add clean solvent. Atomization air should be turned off during this procedure. Pressurize the system and run the solvent through until clean.

NOTICE

Be sure to comply with local codes regarding solvent dispersion and disposal.

Clean the air cap, fluid tip and tank. Reassemble for future use.

39. WHAT PARTS OF THE GUN REQUIRE LUBRICATION?

The A fluid needle packing, the B air valve packing and the C trigger bearing screw require daily lubrication with a non-silicone gun lube.

The D fluid needle spring should be coated lightly with petroleum jelly or a non-silicone grease (ie. Lithium).

The fluid needle spring (E) should be lightly coated with petroleum jelly.

Thoroughly clean the air cap and baffle threads (F), and lubricate with spray gun lube daily.

Lubricate each of these points after **every** cleaning in a gun washer!

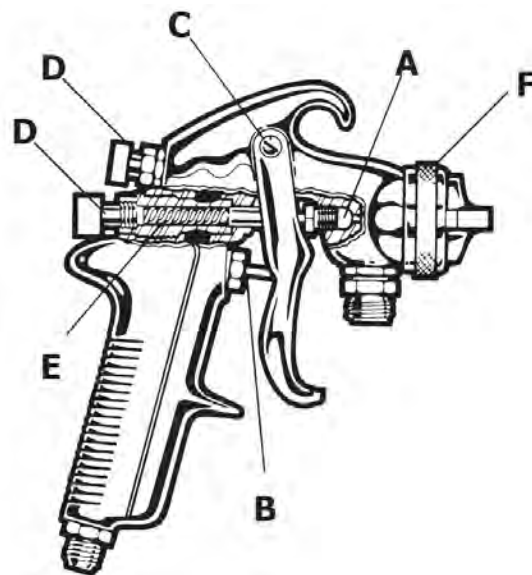


Figure 22: Lubrication Points

TROUBLESHOOTING		
Problem	Cause	Correction
Fluid Leaking From Packing Nut	Packing nut loose	Tighten, do not bind needle
	Packing worn or dry	Replace or lubricate
Air Leaking From Front of Gun	Sticking air valve stem	Lubricate
	Foreign matter on air valve or seat	Replace or lubricate
	Worn or damaged air valve or seat	Replace
	Broken air valve spring	
	Bent valve stem	
	Air valve gasket damaged or missing	
Fluid leaking or dripping from front of pressure feed gun	Packing nut too tight	Adjust
	Fluid tip or needle worn or damaged	Replace tip and needle with lapped or matched sets
	Foreign matter in tip	Clean
	Fluid needle spring broken	Replace
	Wrong size needle or tip	
	Dry packing	Lubricate
Jerky, fluttering spray (Siphon and Pressure Feed)	Material level too low	Refill
	Container tipped too far	Hold more upright
	Obstruction in fluid passage	Backflush with solvent
	Loose or broken fluid tube or fluid inlet nipple	Tighten or replace
	Loose or damaged fluid tip/seat	Adjust or replace
	Dry or loose fluid needle packing nut	Lubricate or tighten
Jerky, fluttering spray (Siphon Feed Only)	Material too heavy	Thin or replace
	Container tipped too far	Hold more upright
	Air vent clogged	Clear vent passage
	Loose, damaged or dirty lid	Tighten, replace or clean coupling nut
	Dry or loose fluid needle packing	Lubricate or tighten packing nut
	Fluid tube resting on cup bottom	Tighten or shorten
	Damaged gasket behind fluid tip	Replace gasket
Top or Bottom-Heavy Spray Pattern*	Horn holes plugged	Clean, ream with non-metallic point (ie. Toothpick)
	Obstruction on top or bottom of fluid tip	Clean
	Cap and/or tip seat dirty	
Right or Left-Heavy Spray Pattern*	Left or right side horn holes plugged	Clean, ream with non-metallic point (ie. Toothpick)
	Dirt on left or right side of fluid tip	Clean

* Remedies for heavy patterns on the top, bottom, right, and left are:

1. Examine the air cap or fluid tip for obstruction. Make a solid test spray pattern to do this test. Rotate the cap one-half turn and spray another pattern.
 - a. If the defect is inverted, obstruction is on the air cap. Clean the air cap as previously instructed.
 - b. If the defect is not inverted, it is on the fluid tip. Examine the edge of the fluid tip for a fine burr. Remove any burrs with #600 wet/dry sand paper.
2. Check for dried paint just inside the opening. Remove dried paint by washing with solvent.

TROUBLESHOOTING (cont.)

Problem	Cause	Correction
Center-Heavy Spray Pattern	Fluid pressure too high for atomization air (pressure feed)	Balance air and fluid pressure Reduce spray pattern width
	Material flow exceeds air cap's capacity	Thin or reduce fluid flow
	Spreader adjustment valve set too low	Adjust
	Atomizing pressure too low	Increase pressure
	Material too thick	Thin to proper consistency
Split Spray Pattern	Fluid adjusting knob turned in too far	Back out counter clockwise to achieve proper flow
	Atomization air pressure too high	Reduce at regulator
	Fluid pressure too low (pressure feed)	Increase fluid pressure Change to a larger tip
Starved Spray Pattern	Inadequate material flow	Back fluid adjusting screw out to first thread or increase fluid pressure
	Low atomization air pressure (siphon feed)	Increase air pressure and rebalance gun
Unable to Form Round Spray Pattern	Fan adjustment stem not seating properly	Clean or replace
Dry Spray	Air pressure too high	Lower air pressure
	Material not properly reduced (siphon feed)	Reduce to proper consistency
	Gun tip too far from work surface	Adjust to proper distance
	Gun motion too fast	Slow down
Excessive Overspray	Too much atomization air pressure	Reduce pressure
	Gun too far from surface	Use proper gun distance
	Improper technique (arcing, gun speed too fast)	Use moderate pace, parallel to work surface
Excessive Fog	Too much, or too fast-drying thinner	Remix properly
	Too much atomization air pressure	Reduce pressure
Will Not Spray	No pressure at gun	Check air lines
	Fluid pressure too low (internal mix cap with pressure tank)	Increase fluid pressure at tank
	Fluid tip not open enough	Open fluid adjusting screw
	Fluid too heavy (siphon feed)	Reduce fluid or change to pressure feed
	Internal mix cap used with siphon feed	Change to external mix air cap
	Pressure feed cap/tip used with siphon feed	Use suction feed cap/tip

PRINCIPLES OF ELECTROSTATICS

Electrostatic spray finishing combines the mechanical process of atomization with the distributive effects of electrical attraction and repulsion to achieve a highly efficient product finishing operation.

Atomization is achieved in liquid systems by air, airless, air-assisted, and rotary apparatus. The coating material is brought into contact with or through the immediate vicinity of highly charged electrodes. As this occurs, a considerable level of electrical charge is transferred either by direct contact or by passage through a highly ionized zone near the gun tip (which can be used up to 100 kV), to the particles or droplets of coating material. Since all the particles or droplets are similarly charged and since like charges repel one another. Pattern in an electrostatic spray process tends to be larger and more evenly distributed than that of a non-electrostatic process. This increases the ease and efficiency.

When a metallic object, which is electrically neutral or grounded is present, the electric field is established between the charging electrodes of the gun and the grounded object which, in this case, is the item we wish to coat. The electrically charged particles or droplets of coating material are attracted via the electric field toward the grounded object in much the same way that iron filings are attracted to a magnet. As the particles or droplets come in contact with the grounded object, they begin to dissipate their electrical charges through the metal of the object.


With a typical electrostatic spray gun, a charging electrode is located at the tip of the atomizer. The electrode receives an electrical charge from a power supply. The paint is atomized as it exits past the electrode, and the paint particles become ionized (pick up additional electrons to become negatively charged)

The degree to which electrostatic force influences the path of paint particles depends on how big they are, how fast they move, and other forces within the spray booth such as gravity and air currents. Large particles sprayed at high speeds have great momentum, reducing the influence of the electrostatic force. A particle's directional force inertia can be greater than the electrostatic field. Increased particle momentum can be advantageous when painting a complicated surface, because the momentum can overcome the Faraday cage effect; the tendency for charged paint particles to deposit only around the entrance of a cavity.

On the other hand, small paint particles sprayed at low velocities have low momentum, allowing the electrostatic force to take over and attract the paint onto the workpiece. This condition is acceptable for simple surfaces but is highly susceptible to Faraday cage problems. An electrostatic system should balance paint particle velocity and electrostatic voltage to optimize coating transfer efficiency. Since the object is grounded through its hanger and conveyor back to electrically neutral earth, the charge does not accumulate in the metal of the object, allowing it to continue to accept more charges from newly arriving particles or droplets of coating material. Since the particles or droplets do not shed all of their charge immediately, and since like charges repel each other, newly driving charged particles or droplets will tend to be repelled from spots that are already coated and attracted to the remaining areas of bare metal. Similarly, particles and droplets that were propelled beyond the grounded object will tend to curve in around behind it, thus giving the "wrap-around" and recess penetration effects associated with electrostatic spray finishing.

If, however, a metallic or otherwise electrically conductive object is in the vicinity which is NOT properly electrically grounded, an entirely different process can occur. Initially, because it is an electrically neutral condition, it will attract the charged particles or droplets of coating material. However, as more and more coating material arrives and shares its charge with the object, the electrical charge will build up in the object because there is no pathway to ground, turning the object into a static electricity "battery". Eventually, and in many cases, this can mean just a few seconds, enough electrical charge can accumulate in the object that a spark can be generated between it and the nearest ground surface. Or, similarly, an ungrounded metallic object can simply retain its electrical charge for an indefinite time until a grounded surface is brought near enough for a spark to occur. This grounded surface can be a swinging conveyor hook or an operator reaching out to touch the charged object. Likewise, a spark can occur between the electrostatic device and itself and a grounded object if the electrodes or other high voltage portion of the device are placed or brought too close to ground.

Lastly, electrostatic spray finishing can also be used on nonconductive or conductive plastics as well as conductive wood objects.

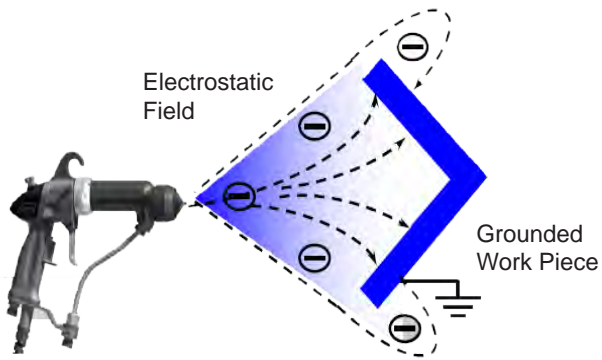

Faraday Cage Effect

ELECTROSTATIC ADVANTAGES

The main benefit offered by an electrostatic painting system is transfer efficiency. In certain applications electrostatic bells can achieve a high transfer efficiency exceeding 90% (see page 32). This high efficiency translates into significant cost savings due to reduced overspray.

A phenomenon of electrostatic finishing known as “wrap” causes some paint particles that go past this workpiece to be attracted to the back of the piece, further increasing transfer efficiency.

Increased transfer efficiency also reduces VOC emissions and lowers hazardous waste disposal costs. Spray booth cleanup and maintenance are reduced.

COATING APPLICATION

Any material that can be atomized can accept an electrostatic charge. Low-, medium-, and high-solids solvent borne coatings, enamels, lacquers, and two-component coatings can be applied electrostatically.

The various types of electrostatic systems can apply coatings regardless of their conductivity. Waterborne and metallic coatings can be highly conductive. Solvent-borne coatings tend to be nonconductive. Any metallic coatings can contain conductive metal particles. These metallic coatings must be kept in circulation to prevent a short circuit in the feed line. As high voltage is introduced into the system, the metal particles can line up to form a conductive path. System modifications may be required because of coating conductivity to prevent the charge from shorting to ground.

OPERATING ELECTROSTATICS SAFETY

Electrostatic finishing is safe if the equipment is maintained properly and safety procedures are followed.

⚠ WARNING

All items in the work area must be grounded, including the spray booth, conveyor, parts hangers, application equipment (unless using conductive/waterborne coatings), and the spray operator.

As electrical charges come in contact with ungrounded components, the charges can be absorbed and stored. This is known as a capacitive charge build up. Eventually, enough charge is built up so that when the ungrounded item comes within sparking distance of a ground, and is charged as a spark. Such a spark may have enough energy to ignite the flammable vapors and mists that are present in the spray area.

An ungrounded worker will not know that the capacitive charge has been absorbed until it is too late. Workers should never wear rubber or cork-soled shoes, which can turn them into ungrounded capacitors. Special shoe grounding devices are available. If workers are using hand-held guns, they should grasp them with bare hands or with gloves with cut-outs for fingertips and palms that allow adequate skin contact.

Proper grounding of all equipment that is not used for the high-voltage process is essential. Grounding straps should be attached to equipment and connected to a known ground. A quick inspection of all equipment, including conveyors and part hangers, can reveal improper grounding.

Good housekeeping can pay dividends. Removing paint build up from parts hangers can help ensure that workpieces are grounded. Ungrounded objects, such as tools and containers, should be removed from the finishing area.

ELECTROSTATIC PROCESS & EQUIPMENT

The electrostatic application of atomized materials was developed to enhance finish quality and improve transfer efficiency.

Presently, there are seven types of electrostatic processes for spray application:

- Electrostatic air spray atomization
- Electrostatic high-volume, low-pressure (HVLP) atomization
- Electrostatic airless atomization
- Electrostatic air-assisted airless atomization
- Electrostatic electrical atomization
- Electrostatic rotary-type bell atomization
- Electrostatic rotary-type disk atomization

Regardless of the electrostatic finishing systems, each has its advantages and limitations. What may be suitable for one situation may not be suitable in another.


ELECTROSTATIC AIR SPRAY ATOMIZATION

Electrostatic air spray uses an air cap with small precision openings that allows compressed air to be directed into the paint for optimum atomization. Electrostatic air spray is the most widely used type of atomization in the industry today due to its control and versatility. Electrostatic air spray provides very high transfer efficiency by utilizing the electrostatic charge to wrap paint around edges and capture overspray that would have been unusable waste. Standard electrostatic air spray provides transfer efficiencies in the 40 to 75% range depending on the type of material and application.

ELECTROSTATIC HVLP SPRAY ATOMIZATION

Electrostatic HVLP spray utilizes the same atomization characteristics as electrostatic air spray technology with slight modifications. When using air HVLP, the pressure of the compressed air at the air cap must be reduced to a range of 0.1 to 10 psi.

Transfer efficiency is greater when using HVLP spray to lower the particle velocity and atomize the material thus causing less waste and blow-by of material. Some electrostatic equipment can be easily converted or transformed between air spray and HVLP spray technology by simply changing four parts. HVLP spray technology helps meet stringent EPA codes requiring reduced VOCs and waste. Electrostatic HVLP spray provides transfer efficiencies in the 40 to 80% range depending on the type of material and application.

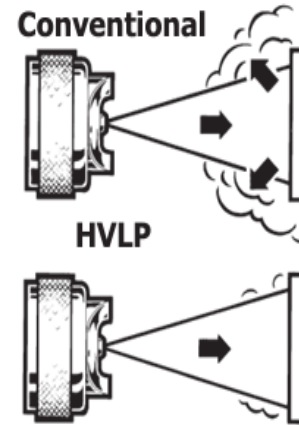


Air Spray Atomization Technology

ELECTROSTATIC AIRLESS SPRAY ATOMIZATION

Electrostatic airless spray technology utilizes the principle of fluid at high pressures (500-5,000 psi) atomizing through a very small fluid nozzle orifice. Size and shape of the spray pattern, along with fluid quality is controlled by the nozzle orifice. Airless spray technology evolved after air spray to aid in faster application rates using higher delivery and heavier viscosities on larger parts.

ELECTROSTATIC AIR ASSISTED AIRLESS ATOMIZATION

Electrostatic air-assisted airless spray technology uses the airless spray principle to atomize the fluid at reduced fluid pressure with assisted atomizing air to aid in reducing pattern tailing and affect pattern shape. Air-assist airless spray technology offers some of the desirable characteristics of both airless spray and air spray; the desirable characteristics being medium to high delivery rates, ability to spray heavy viscosities at low velocities, and high transfer efficiency.

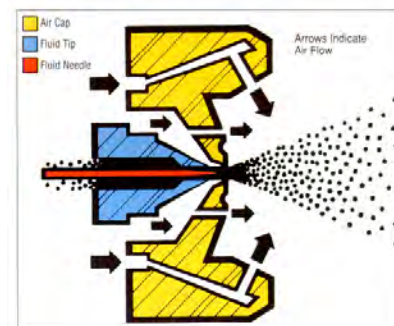

This is where atomization takes place! Air cap and fluid tip design are the key factors in atomization and transfer efficiency

ELECTROSTATIC ELECTRICAL ATOMIZATION

Electrostatic electrical atomization is accomplished by using a rotary bell on the end of a gun to evenly dispense paint to the edge of the bell. Once the coating material reaches the edge of the bell it is introduced to an electrical charge. The electrical charge at the sharp edge (approximately 100 kV) causes paint of a medium electrical resistance range (0.1 to 1 megohms) to disperse onto the product. The pure electrical application is a slightly slower process than an air spray or air-assisted airless technology and requires a rotational type spray paint technique, due to the bells spray pattern, but is the most transfer efficient spray gun process in the industry today. The ultrasoft forward velocity of the spray pattern achieves transfer efficiencies of nearly 100% on most products.

This high transfer efficiency spawned the industry of painting and refurbishing machinery and furniture in place.



ELECTROSTATIC ROTARY BELL ATOMIZATION

An electrostatic bell atomizer is a high-speed rotary bell that uses centrifugal force and mechanical shearing to atomize material and efficiently transfer material from the bell edge to the target being painted.

The bell is used on a turbine motor where the pattern is carefully directed by the use of compressed air, introduced to the pattern at the edge of the bell cup. The compressed air gives the material forward velocity to aid in penetrating recessed areas. The bells are usually mounted stationary, reciprocated or on robots to coat products on straight line conveyors. The bells may also be positioned on both sides of the conveyor. Rotary type bell atomization provides transfer efficiencies in the 60 to 85% range.



ELECTROSTATIC ROTARY DISK ATOMIZATION

An electrostatic rotary-disk atomizer is a high-speed rotary atomizer that uses centrifugal force along with mechanical shearing to atomize coating material and efficiently transfer the material from the disk edge to the target being painted.

The disk is used in an omega shape loop conveyor to coat the product. Disks may be mounted stationary and tilted (up to 45°) to coat small parts of 12 in. or less, or mounted on reciprocating arms to coat parts up to 40 ft. in height but generally no wider than 4 ft. in width. The disk produces transfer efficiencies in the 70 to 95% range.



ELECTROSTATIC POWDER APPLICATION

It is worth noting that using powder instead of liquid has also recently been developed as another technology to enhance finish quality, improve transfer efficiency and lower VOC's. Powder application utilizes a similar electrostatic processes versus liquid applications.

Electrostatic powder technology utilizes power from a controller to power a cascade that generates a high voltage charge to the electrode on the end of a gun. Once the powder reaches the end of the gun it is introduced to the high voltage charge.

The high voltage differential between the grounded work piece and the electrode of the coating gun generates an electric field, which transmits a negative charge on the individual powder particles.

Since these particles have the same charge as the spray gun, they are repelled, distributed in a fine cloud and deposited evenly on the grounded work piece. Powder that does not initially make contact with the work piece is caught in the electrical field and wraps around to the backside of the work piece.

Powder coating technology provides effective material utilization, time savings, improved coating quality, less cleaning effort and a healthy working environment.

OPERATING ELECTROSTATIC COATING SYSTEMS SAFELY

PERSONNEL GROUNDING

⚠ CAUTION

The integrity of the system ground **MUST** be inspected regularly and maintained. It is simple, but **VITAL** to be sure that all objects in an electrostatic coating area are grounded (reference NFPA-33).

SAFETY

Inspect all grounded wires daily. Look for good, firm joints at all points of connection (paint pots, flow regulators, booth wall, power supply, etc.). Look for breaks in the ground wire.

Repair any defect **IMMEDIATELY!**

Inspect all conveyor apparatus (hooks, hangers, etc.) daily. If there is any accumulation of dried coating material on any of these objects, remove it before using them!

Inspect the floor daily for excessive accumulation of dried coating material (or other residue). If there is any, remove it!

NOTICE

Safe grounding is a matter of proper equipment maintenance, proper spray technique, and good housekeeping

Daily inspection of grounding apparatus and conditions, however, will help prevent hazards that are caused by normal, daily operations.

Personnel grounding is the most difficult area of electrical hazard control. Most people do not realize what excellent capacitors they are. In a very short time, without proper grounding, the human body can build enough static charge to cause dangerous spark discharge.

⚠ WARNING

ALL persons in an electrostatic coating area **MUST** be grounded at **ALL** times!

Manual equipment operators will be grounded through the equipment as long as it is being held in contact with the bare skin. As soon as the equipment is released from direct (skin) contact with the operator, other grounding methods becomes necessary.

SAFETY

The operator **SHOULD NOT** wear insulating gloves! Special conductive gloves may be used and are recommended.

If insulating (cloth or rubber) gloves are worn, both palms **MUST** be cut out to allow bare skin contact with the equipment! This allows the operator to change the equipment from one hand to the other.

If gloves are worn for chemical safety, grounding wrist straps may be connected from the operator's wrist to the gun assembly.

⚠ WARNING

ALL persons in an electrostatic coating area **MUST** be grounded at **ALL** times!

This may be accomplished safely by the use of conductive soled shoes, disposable conductive boots, or personnel grounding straps.

EQUIPMENT GROUNDING

In electrostatic coating systems, the flow of high voltage power from the power supply to the atomizing head of the gun is insulated from ground and isolated from all other functions and equipment. When the voltage reaches the atomizer, it is transferred to the coating material where, by introducing a (normally) negative charge, it causes the atomized fluid to seek the nearest (normally) positive ground. In a properly constructed and operated system, that ground will be the target object.

The directed conduction of the electric charge through its array of wires, cables, and equipment is accompanied by a variety of stray electrical charges passing through the air by various means such as air ionization; charged particles in the air and radiated energy. Such stray charges may be attracted to any conductive material in the spray area. If the conductive material does not provide a safe drain to electrical ground, which will allow the charge to dissipate as fast as it accumulates, it may store the charge.

When its electrical storage limit is reached, or when it is breached by external circumstances (such as the approach of a grounded object or person, or one at lower potential), it may discharge its stored charge to the nearest ground. If there is no safe path to ground (such as a ground wire) it may discharge through the air as a spark. A spark may ignite the flammable atmosphere of a spray area.

The hazard area extends from the point of origin up to as much as a twenty foot radius. See the NFPA-33 for definition and limitations of "hazard area".

NOTICE

It is a simple, but vital matter to be sure that ALL conductive objects within the spray area are grounded. This will include such items as, but are not limited to: cabinets, benches, housings, ladders, bases, containers, stands, people, and product. ALL of which are not by design, insulated from ground **MUST** be connected directly and **INDIVIDUALLY** to true earth ground. Resting on a concrete floor or being attached to a building column may not always be sufficient ground.

- In order to provide the best ground connection possible, always attach a ground wire to the terminal indicated by the ground symbol and then to a proven, true earth ground.
- Always check ground connections for integrity. Some items, such as rotators and paint stands, may be supported on insulators, but all components of the system up to the insulator **MUST** be grounded.
- It is recommended that ground wires be made of No. 18, bare, stranded wire (minimum). Where possible, use larger wire.
- Where items are mounted directly on structural components such as building columns, the ground connection **MUST** still be made.
- In many cases the structural component may be painted or coated with an insulating material, and in many cases the equipment will be painted. These coatings are insulating. The ground connection must be as perfect as possible.

GUN GROUNDING**⚠ WARNING**

The high voltage **MUST** be OFF and **GROUND**ED before any direct personal contact is made with equipment.

Procedures to be followed for safely conducting electrostatic coating operations are outlined in “Operating Your Electrostatic Coating System Safely” section in this Service Manual.

Electrostatic systems depend on high voltage to atomize coating material and deposit it on the target object. During operation, the system is at high voltage. Personnel must **NEVER** attempt any direct contact with the equipment **UNTIL** the high voltage is OFF, the atomizer has **STOPPED** rotating and the ground hook has been attached to the gun or paint supply as indicated. The ground hook cable **MUST** be secured to a proven, true earth ground and readily accessible to the gun or paint supply.

A ground hook is designed to be used with disk or bell atomizers or with insulated fluid suppliers. In addition to the aluminum hook, the standard assembly has 15 feet of aircraft cable and a solderless connector for mounting. One assembly should be conveniently located at each station. After the high voltage is off and the atomizer has stopped, the hook should be touched to the atomizer hub or gun housing momentarily to dissipate any residual charge. It should then be hooked to the gun housing.

DO NOT allow the hook or its cable to touch the working edge of a disk or bell atomizer. This edge is critical to good atomization and should **ALWAYS** be protected from any contact that might cause even the slightest damage. For overhead applicators it may be necessary to suspend the cable with a spring or other elastic material in order to prevent edge contact. Most Waterborne Fluid Supply Enclosures include an insulated paint stand plus a grounded chain link enclosure, and a gate that is equipped with a limit switch, switch trip and control box. The enclosure is also equipped with a standard ground hook assembly to ground the paint supply when personnel are inside of the enclosure.

Personnel entering an insulated fluid supply enclosure **MUST FIRST** be sure that the system is **NOT** operating. After entering the enclosure, the ground hook must be attached to the paint supply **BEFORE** any personal contact is made. The ground hook **MUST** be attached during all service and above all, during the addition of fluid to the supply container! When leaving the enclosure remove the ground hook and close and secure the gate. The warning light **MUST** be **ON** whenever the system is operating.

Ground **MUST** be maintained during the addition of fluid to any supply container! Whenever transferring flammable fluid from one container to another, both containers **MUST** be properly connected to a proven ground first and then to each other. Personnel executing such a transfer must also be grounded. An appropriate number of ground hook assemblies are included with systems that require them.

NO. 2 HAND GUN GROUNDING ON SITE PAINTING

For over 50 years the No. 2 Process hand gun has been the most widely used tool by on-site painting industry for the refinishing of office furniture, office panels, lockers, school furniture, and dozens of other items.

Quite often we are asked about the dangers and possible damage to computers, phone systems, or electronically keyed security systems when electrostatic painting is done nearby.

Concerning those types of applications, the following facts should be noted:

1. The No. 2 Process hand gun is not electromagnetic. It is electrostatic (much like the static from carpets or wool and synthetic clothing), and works at an output of 100 kilovolts at 30-50 microamperes current draw (100 microamperes maximum short circuit current).

NOTICE

Grounding of all conductive objects near an electrostatic spray gun is of utmost importance.


2. Unlike x-rays, "electrostatics" does not go "through" objects.
3. Some computers and phone systems are now shielded by the manufacturer against outside static.
4. If the static shielding of the unit is unknown, the keyboard, CPU (central processing unit) and its cable preferably should be removed from the immediate painting area for protection of the device. If this is not feasible they should be completely wrapped in aluminum foil that is grounded to an earth ground. This will create a "Faraday cage" around the computerized device.
5. Electrical sparks of all types create an R.F. energy (radio frequency) that may radiate through the air and enter into electronic circuits. The resulting damage is unpredictable.

6. Computer software such as tapes, disks, diskettes, etc., should be removed from inside and the immediate surrounding area of any enclosures that are to be painted.
7. Lightning or electrostatic voltage sparking into an A.C. circuit can create "spikes" or electromagnetic pulse (EMP) that can cause unpredictable damage to electronic hardware.
8. Surge suppressors are available that may help protect appliances from "spikes" of current if the suppressor is in the A.C. line supplying the appliance.
9. When painting any type of electrical control panel or console it is generally not known if all pushbuttons, switches, meters or pilot lights are properly grounded. In view of this, it is desirable to cover all of these items with aluminum foil, which is grounded to the panel or another earth ground.
10. All on-site painting companies should have adequate liability insurance to protect them in the event of any real or perceived damage as a result of their operations.

NOTICE

In view of the above unknown and possible uncontrolled conditions, Ransburg does not recommend the electrostatic painting of computer cabinets, consoles or painting in close proximity to these devices.

Percent Efficiency By Spray System Type

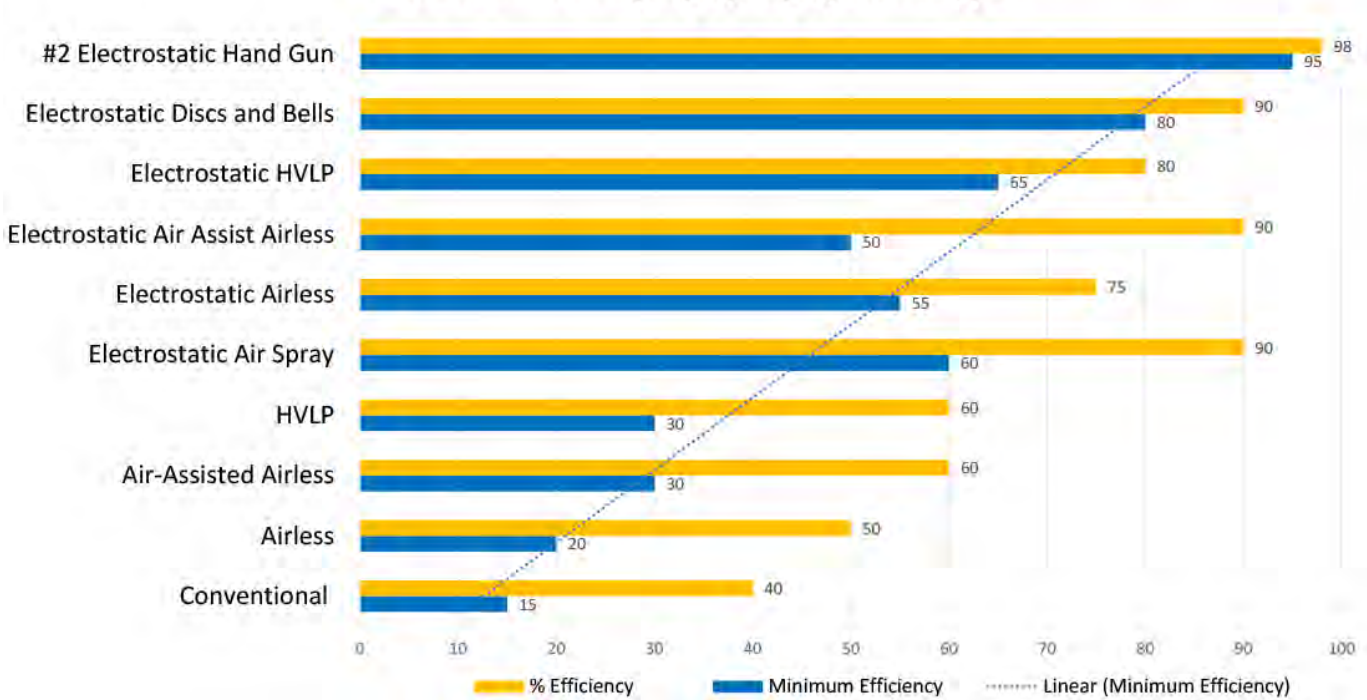

NOTICE

All figures are considered "baseline". Actual transfer efficiency varies due to an unlimited number of variables. Conditions may vary due to material and application.

INTRODUCTION

All spray painting systems from the smallest brush to the most sophisticated finishing system must have containers to hold the material being applied.

Material container types and sizes vary considerably, depending on the kind of spraying system being used.

This chapter will discuss these containers, their particular applications, their construction and maintenance.

1. WHAT ARE MATERIAL CONTAINERS?

Any container which serves as a material supply reservoir for the spray gun. These containers are usually made of metal or plastic with capacities of 1/2 pint or more.

2. WHAT ARE THE TYPES OF MATERIAL CONTAINERS?

There are three common types of cups which attach to the gun itself: Siphon, Gravity and Pressure.

There are also remote pressure cups and tanks, which are located away from the gun. See Page 11 for types of guns and systems.

3. WHAT ARE CUP CONTAINERS?

Cup containers are typically one quart or less, and are used where relatively small quantities of material are being sprayed.

4. HOW ARE MATERIAL FEED CUPS ATTACHED TO LID ASSEMBLIES?

Cups are attached using a lid assembly (sometimes called a cup attachment) that either clamps A or screws B onto the cup container. (see Figure 1) Some lid assemblies are detachable from the gun, while others are integral parts and do not detach from less expensive models.

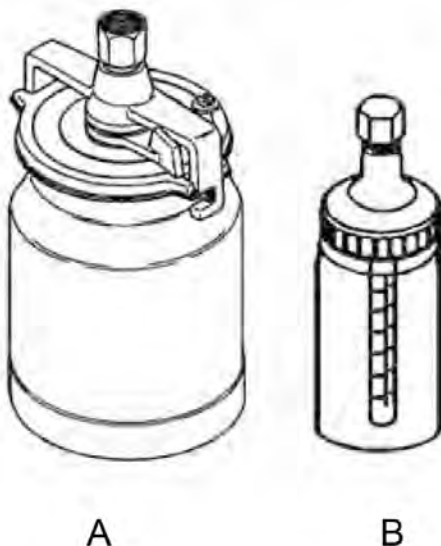


Figure 1: Cup Attachment Styles

5. WHAT CAPACITY DOES A PRESSURE FEED CUP HAVE?

A pressure feed cup can have a one or two quart capacity. Anything larger is considered a pressure feed tank, which may be positioned some distance from the gun.

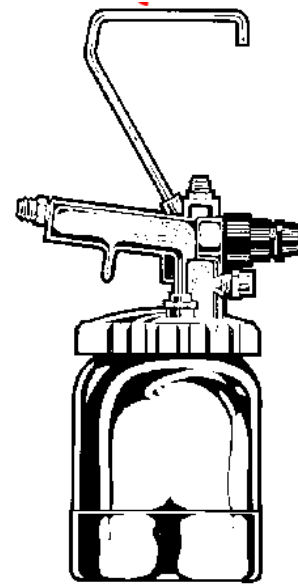


Figure 2: Regulated 2 Qt. Pressure Cup

6. HOW DO PRESSURE FEED TANKS WORK?

Pressure feed tanks are closed containers, ranging in size from about two gallons to 60 gallons. They provide a constant flow of material, under constant pressure, to the spray gun.

The tank is pressurized with clean, regulated, compressed air, which forces the fluid out of the tank through the fluid hose to the gun.

The rate of fluid flow is controlled by increasing or decreasing the air pressure in the tank.

A typical pressure feed tank consists of:

- a) the shell
- b) a clamp-on lid
- c) the fluid tube
- d) the fluid header
- e) regulator
- f) gauge
- g) a safety relief valve
- h) agitator

Pressure feed tanks are available with either top or bottom fluid outlets, and with various accessories.

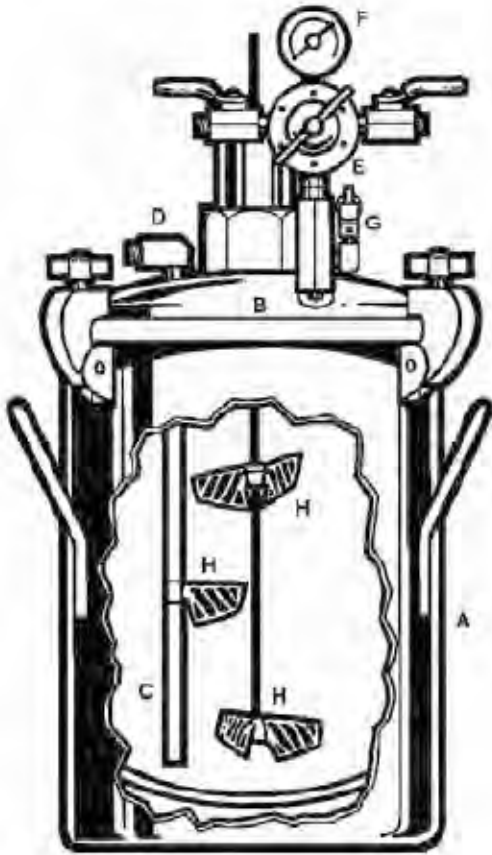


Figure 3: Pressure Feed Tank

7. WHY ARE PRESSURE FEED TANKS RECOMMENDED?

Pressure feed tanks provide a practical, economical method of material feed to the gun over extended periods of time.

They are mostly used in continuous production situations, because the material flow is positive, uniform and constant.

Tanks can be equipped with agitators (see Figure 3) that keep the material mixed and in suspension.

8. WHEN IS AN AGITATOR USED IN A PRESSURE FEED TANK?

When the material being used has filler or pigment that must be kept in motion to keep its particles in proper suspension. An agitator can be hand, air or electrically driven.

9. WHAT IS A SINGLE REGULATED TANK?

This is a pressure feed tank with one air regulator controlling only the pressure on the material in the tank.

An extra-sensitive regulator is available for use with lower fluid flow and/or lower viscosity material where precise control is needed.

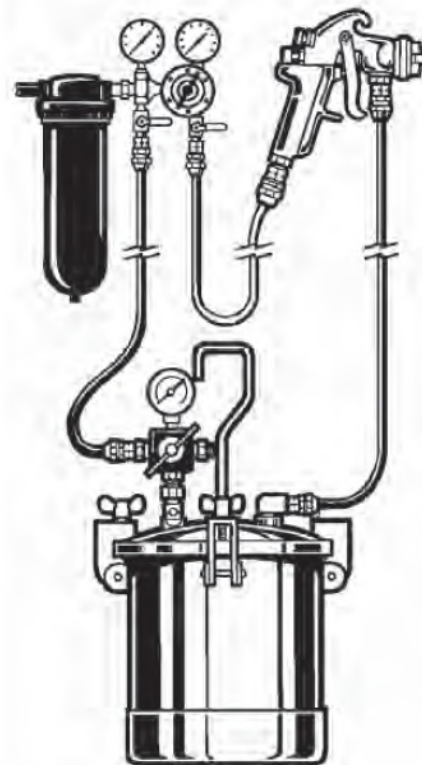


Figure 4: Single Regulated Tank

10. WHAT IS A DOUBLE REGULATED TANK?

This is a pressure feed tank equipped with two air regulators.

One provides regulation for the air pressure on the material in the tank (thereby controlling fluid flow). The other controls atomization air pressure to the spray gun.

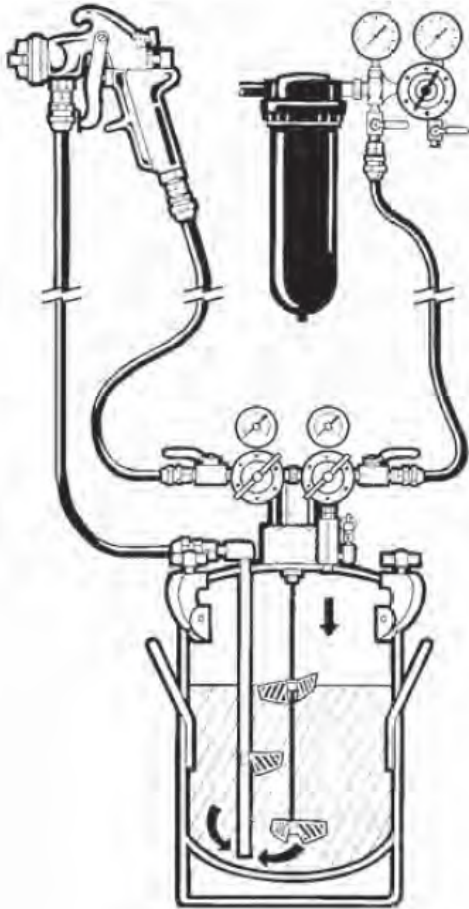


Figure 5: Double Regulated Tank

11. WHAT ARE CODE AND NON CODE PRESSURE TANKS?

Code tanks are manufactured to rigid standards as specified by the American Society of Mechanical Engineers. (ASME) Each step of manufacture is closely controlled, and welding of the shell is certified. Code tanks are designed to withstand pressures up to 80 or 110 psi.

Non-code tanks are normally restricted to 3 gallons in size or less. Due to the type of construction, non-code tanks are rated at 80 psi or less.

12. WHAT MATERIALS ARE USED TO CONSTRUCT PRESSURE FEED TANKS?

The smaller, non-code, light-duty tanks are made of plated steel and have lower inlet pressure restrictions.

The heavy-duty, ASME-code tanks are made of galvanized or 300 series stainless steel. They also have pressed or stainless steel lids with forged steel clamps.

When abrasive or corrosive materials are being sprayed, the tank shell is coated or lined with a special material, or a container insert is used.

13. WHAT ARE CONTAINER INSERTS?

They are liners that are placed inside the tank to hold the material, keeping it from direct contact with the tank walls. They are made of disposable polyethylene.

Using inserts reduces tank cleaning time and makes color changeover easier. They also allow multiple batches of material to be mixed in advance.

You may want to consider stainless steel "Inner containers" when using ceramics or corrosive materials.

Another option to consider is putting the coating container directly into the tank if room allows. Be sure that the tank "pickup tube" does not touch the bottom of the coating container inserted into the tank.

14. WHEN WOULD YOU USE A BOTTOM OUTLET TANK?

- When you are using more viscous materials.
- When continuous, steady pressure is required, such as when feeding plural component proportioning equipment.
- When you wish to use all the material in the tank and you are not using an insert.

15. WHAT WOULD I USE IF I HAVE DIFFICULTY ACCURATELY SETTING LOWER FLUID PRESSURES?

An extra-sensitive regulator is available for use with lower fluid flow and/or lower viscosity materials where precise control is needed.

INTRODUCTION

The various types of hose used to carry compressed air and fluid material to the spray gun are important parts of the system.

Improperly selected or maintained hose can create a number of problems. This chapter will review the different kinds of hose and fittings in use, provide guidance in selecting the proper types for the job and cover the maintenance of hose.

1. WHAT TYPES OF HOSE ARE USED IN SPRAY PAINTING?

There are two types:

- air hose - used to transfer compressed air from the air source to the gun and
- fluid hose - used only in pressure feed systems to transfer the material from its container to the spray gun.

NOTICE

Do not use air hose for solvent-based materials.

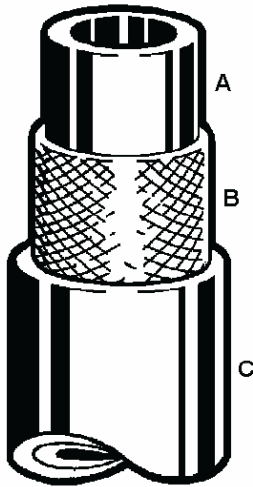


Figure 1: Basic Hose Construction

2. HOW IS THE HOSE CONSTRUCTED?

Binks/DeVilbiss hose is a performance designed combination of three components; A Tube, B Reinforcement and C Cover.

The tube is the interior flexible artery that carries air or fluid material from one end of the hose to the other.

The reinforcement adds strength to the hose. It is located between the tube and cover, and it can be many combinations of materials and reinforcement design. Its design determines pressure rating, flexibility, kink and stretch resistance and coupling retention.

The cover is the outer skin of the hose. It protects the reinforcement from contact with oils, moisture, chemicals and abrasive objects. The cover protects the reinforcement, but does not contribute to hose performance.

SAFETY

Hose color coding is as follows:

- Red or Tan: Air and water
- Grey: Air with static ground
- Black: Low pressure fluid
- Tan: Conductive

3. WHAT TYPE OF TUBE IS USED IN THE FLUID HOSE?

Since the solvents in coatings would readily attack and destroy ordinary rubber compounds, fluid hose is lined with special nylon solvent-resistant material that is impervious to common solvents.

4. WHAT SIZE OF FLUID HOSE ARE RECOMMENDED?

Figure 2: Recommended Fluid Hose Sizes

Type	Length	Size
General Purpose	0'-20'	1/4" ID
	10'-35'	3/8" ID
	35'-100'	1/2" ID
	100'-200'	3/4" ID

5. WHAT SIZES OF AIR HOSE ARE RECOMMENDED?

The hose from the regulator to a gun or tank should be a minimum of 5/16" ID. Tools requiring more air may need 3/8" ID hose or larger.

Figure 3: Recommended Air Hose Sizes

Type	Length	Size
Air Tools	0'-10'	1/4" ID
General Purpose	10'-20'	5/16" ID
	20'-50'	3/8" ID
	50'-100'	1/2" ID
HVLP	0' to 20'	5/16" ID
	20' - 50'	3/8" ID
	50'-100'	1/2" ID

6. WHAT IS PRESSURE DROP?

This is the loss of air pressure due to friction (caused by air flow) between the source of the air and the point of use. As the air travels through the hose or pipe, it rubs against the walls. It loses energy, pressure and volume as it goes.

7. HOW CAN THIS PRESSURE DROP BE DETERMINED?

At low pressure, with short lengths of hose, pressure drop is not particularly significant. As pressure increases, and hose is lengthened, the pressure rapidly drops and must be adjusted.

All air hose is subject to pressure loss or drop. For example, 1/4" pressure drop is 1 psi per foot and 5/16" is 1/2 psi per foot. This pressure loss may result in poor atomization.

Too often, a tool is blamed for malfunctioning, when the real cause is an inadequate supply of compressed air due to an undersized ID hose.

NOTICE

For optimum spray gun results, the following is recommended: up to 20 ft - 5/16" I.D. only over 20 ft - 3/8" I.D.

8. HOW ARE HOSES MAINTAINED?

Hoses will last a long time if they are properly maintained.

SAFETY

Be careful when dragging hose across the floor. It should never be pulled around sharp objects, run over by vehicles, kinked or otherwise abused. Hose that ruptures in the middle of a job can ruin or delay the work.

Proper hose cleaning techniques are covered on page 22. The outside of both air and fluid hose should be occasionally wiped down with solvent. At the end of every job, they should be stored by hanging up in coils.

9. WHAT KINDS OF HOSE FITTINGS ARE AVAILABLE?

Permanent, crimp type or reusable fittings are used to connect hoses to air sources or to spray equipment.

10. WHAT KIND OF HOSE CONNECTIONS ARE AVAILABLE?

Although there are many different styles, the two most common are the threaded and the quick-disconnect types.

Remember that elements added to any hose, such as elbows, connectors, extra lengths of hose, etc., will cause a pressure drop.

On HVLP systems, quick-disconnects must have larger, ported openings to deliver proper pressure for atomization. Because of normal pressure drop in the devices, they are not recommended for use with HVLP.

11. WHAT IS A THREADED TYPE CONNECTION?

This is a common swivel-fitting type that is tightened with a wrench.

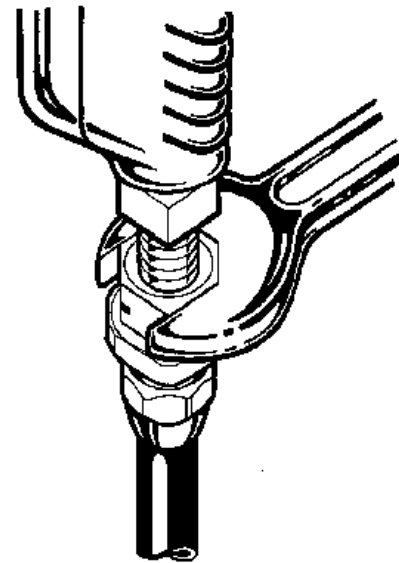


Figure 4: Threaded Type Connection

12. WHAT IS A QUICK DISCONNECT TYPE CONNECTION?

This is a spring-loaded, male/female connection system that readily attaches and detaches by hand. No tools are required.

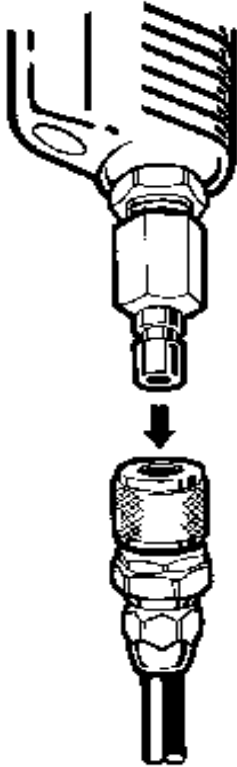


Figure 5: Quick Disconnect (QD) Type Connection

NOTICE

Care should be taken when selecting a quick, detachable air connection. Due to design, most quick disconnects (QD) result in significant pressure drop.

This can adversely affect spray guns with higher consumption air caps such as HVLP.

13. WHAT KIND OF THREADED STYLES ARE AVAILABLE?

Pipe threads made in the United States are different from the pipe threads made in the United Kingdom. In the United States and Canada NPT (National Pipe Taper) threads are primarily used in industry applications.

In the United Kingdom and a majority of the world BSPP (British Standard Pipe Parallel) threads are primarily used in industry applications.

The main difference is the thread angle. It is not recommended to connect NPT and BSPP together as this will cause leaks and damage the threads because they are not compatible.

Additionally, there are two other popular threads you may come across, NPS (National Pipe Straight) and BSPT (British Standard Pipe Taper). NPS threads are straight/parallel when compared to NPT. BSPT threads are tapered when compared to BSPP.

Lastly, there is a high probability that you will come in contact with different threads on components that need to be connected together if these parts were manufactured in different countries.

INTRODUCTION

The control of the volume, the pressure and the cleanliness of the air entering the spray gun are of critical importance to the performance of the system.

Following some key installation principles will help decrease the risk of contaminants. For example, it's important to use the right size air compressor for your application. An overworked air compressor can produce a significant amount of dirt and oil. Additionally, proper piping is very important to help prevent condensation from forming within the line and contaminating the air supply.

This chapter examines the various types of equipment available to perform these control functions.

1. WHAT IS AIR CONTROL EQUIPMENT?

Any piece of equipment installed between the air source and the point of use that modifies the nature of the air stream.

2. WHY IS AIR CONTROL EQUIPMENT NECESSARY?

Raw air, piped directly from an air source to a spray gun, is of little use in spray finishing. Raw air contains small, but harmful, quantities of water, oil, dirt and other contaminants that will alter the quality of the sprayed finish. Raw air will likely vary in pressure and volume during the job.

There will probably be a need for multiple compressed air outlets to run various pieces of equipment.

Any device, installed in the air line, which performs one or more of these functions, is considered to be air control equipment.

3. WHAT ARE THE TYPES OF AIR CONTROL EQUIPMENT?

Air control equipment comes in a wide variety of types, but it basically all performs one or more of the following functions; air filtering/cleaning, air pressure regulation/indication and air distribution through multiple outlets.

4. HOW DOES AN AIR FILTER WORK?

It filters out water, oil, dust and dirt before they get on your paint job. Air entering the filter is swirled to remove moisture that collects in the baffled quiet zone.

Smaller impurities are filtered out by a filter. Accumulated liquid is carried away through either a manual or automatic drain.

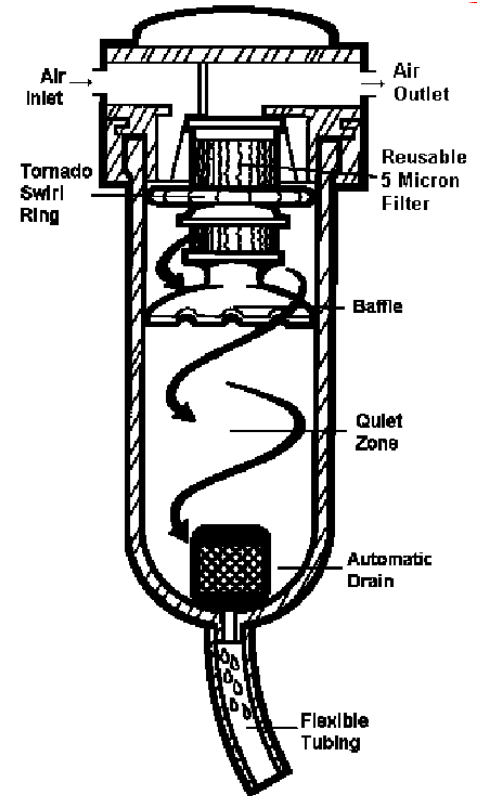


Figure 1: Air Filter

5. WHAT IS AN AIR REGULATOR?

This is a device for reducing the main line air pressure as it comes from the compressor. Once set, it maintains the required air pressure with minimum fluctuations.

Regulators are used in lines already equipped with an air filtration device.

Air regulators are available in a wide range of cfm and psi capacities, with and without pressure gauges and in different degrees of sensitivity and accuracy.

They have main line air inlets and regulated or non-regulated air outlets.

6. HOW IS AN AIR FILTER/REGULATOR INSTALLED?

Bolt (A) the air filter/regulator securely to the spray booth. (see Figure 2)

This location makes it convenient to read the gauges and operate the valves. Install the filter/ regulator at least 25 feet from the (B) compressed air source. Install the (C) takeoff elbow on top of the (D) main air supply line.

Piping should slope back toward the compressor, and a (E) drain leg should be installed at the end each branch, to drain moisture from the main air line.

Use piping of sufficient I.D. for the volume of air being passed, and the length of pipe being used.

7. HOW OFTEN SHOULD THE FILTER/REGULATOR BE DRAINED OF ACCUMULATED MOISTURE AND DIRT?

It depends largely on the level of system use, the type of filtration in the air system, and the amount of humidity in the air.

For average use, once-a-day drainage is probably sufficient.

For heavily-used systems, or in high humidity, drainage should occur several times daily.

Some units drain automatically when moisture reaches a predetermined level.

8. WHAT STEPS SHOULD BE TAKEN IF MOISTURE PASSES THROUGH THE FILTER/REGULATOR?

Since moisture in the spray gun atomization air will ruin a paint job, it must be removed from the air supply.

When the compressed air temperature is above its dew point temperature, oil and water vapor will not condense out into solid particles.

Check the following:

- Drain filter, air receiver and air line of accumulated moisture.
- Be sure the filter is located at least 25 feet from the air source.
- Main air line should not run adjacent to steam or hot water piping.
- Compressor air intake should not be located near steam outlets or other moisture-producing areas.
- Outlet on the air receiver should be near the top of the tank.
- Check for damaged cylinder head or leaking head gasket, if the air compressor is water cooled.
- Intake air should be as cool as possible.

9. WHAT CAUSES EXCESSIVE PRESSURE DROP ON THE MAIN LINE GAUGE OF THE FILTER/REGULATOR?

- The compressor is too small to deliver the required air volume and pressure for all tools in use.
- The compressor is not functioning properly.
- There is leakage in the air line or fittings.
- Valves are partially opened.
- The air line, or piping system, is too small for the volume of air required. Refer to page 37.

Table 1: Minimum Pipe Size Recommendations			
Compressor		Main Air Line	
HP	CFM	Length	Size
1 1/2 - 2	6-9	Over 50'	3/4"
3-5	12-20	Up to 200'	3/4"
		Over 200'	1"
5-10	20-40	Up to 100'	3/4"
		100' to 200'	1"
		Over 200'	1 1/4"
10-15	40-60	Up to 100'	1"
		100' to 200'	1 1/4"
		Over 200'	1 1/2"

NOTICE
Piping should be as direct as possible. If a large number of fittings are used, larger I.D. pipe should be installed to help overcome excessive pressure drop.

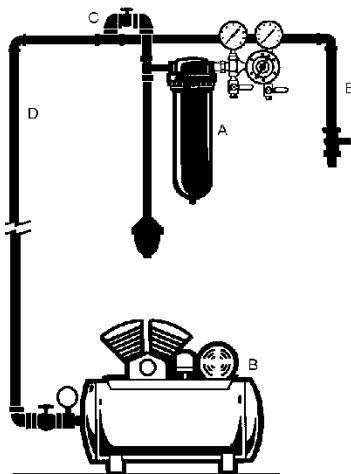


Figure 2: Air/Filter Regulator Installation

INTRODUCTION

Spray finishing creates a certain amount of overspray, hazardous vapors and toxic fumes. This is true, even under ideal conditions, and there is no way to avoid it entirely.

Anyone near a spray finishing operation should use some type of respirator, or breathing apparatus.

This chapter covers various types of equipment for this use.

1. WHAT IS A RESPIRATOR?

A respirator is a mask that is worn over the mouth and nose to prevent the inhalation of overspray fumes and vapor.

2. WHY IS A RESPIRATOR NECESSARY?

For two reasons:

Concerning those types of applications, the following facts should be noted:

1. Respiratory protection is required by OSHA/NIOSH regulations.
2. Even if it wasn't a requirement, common sense tells you that inhaling overspray is not healthy.

Overspray contains toxic particles of paint pigments, harmful dust and vapor. Exposure to any of the above is a potential health risk. Depending on design, a respirator can remove some, or all, of these dangerous elements from the air around a spray finishing operator.

3. WHAT TYPES OF RESPIRATORS ARE USED BY SPRAY FINISHING OPERATORS?

There are three primary types; the air-supplied respirator, the organic vapor respirator and the dust respirator.

4. WHAT IS AN AIR SUPPLIED RESPIRATOR?

This type is available in both mask and visor/hood styles. Both provide the necessary respiratory protection when using materials that are not suitable for organic vapor respirators.

The visor/hood style provides a greater degree of coverage to the head and neck of the operator.

Both styles require a positive supply of clean, breathable air as defined by OSHA (Grade D).



Figure 1: Positive Pressure Visor/Hood

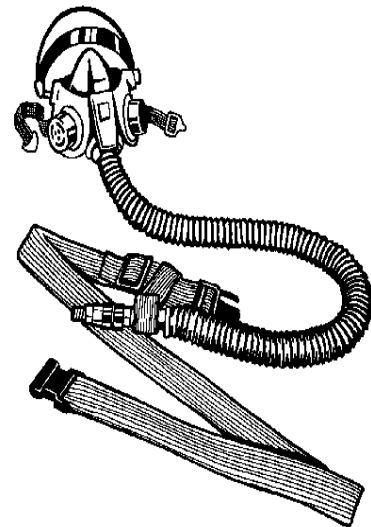


Figure 2: Positive Pressure Mask Respirator

5. WHAT IS AN ORGANIC VAPOR RESPIRATOR AND WHERE IT IS USED?

This type of respirator, which covers the nose and mouth, (see Figure 3) is equipped with a replacement cartridge that removes the organic vapors by chemical absorption.

Some are designed with a prefilter to remove solid particles from the air before it passes through the chemical cartridge.

The organic vapor respirator is usually used in finishing operations with standard materials. (not suited for paints containing isocyanates).

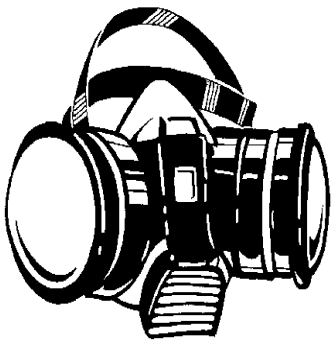


Figure 3: Organic Vapor Respirator

6. WHAT IS A DUST RESPIRATOR AND WHERE IS IT USED?

Dust respirators are sometimes used in spray finishing but, in most applications, they are unsatisfactory. (see Figure 4)

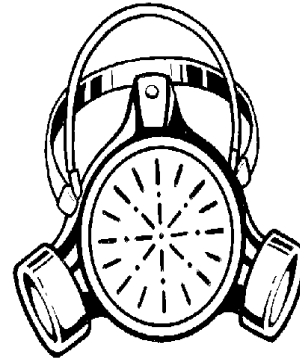


Figure 4: Dust Respirator

These respirators are equipped with cartridges that remove only solid particles from the air. They have no ability to remove vapors.

They are effective, however, in preliminary operations such as sanding, grinding and buffing.

NOTICE

Before using any respirator, carefully read the manufacturer's Safety Precautions, Warnings and Instructions. Many respirators are not suitable for use with isocyanates, asbestos, ammonia, pesticides, etc.

INTRODUCTION

All air tools, spray guns, sanders, etc., must be supplied with air which is elevated to the higher pressures and is delivered in sufficient volume. The air compressor compresses air for use in this equipment and is a major component of a spray painting system. This chapter will examine the various types available.

Compressed air is measured on the basis of the volume supplied per unit of time (cubic feet per minute, or cfm) at a given pressure per square inch (psi), referred to as delivery.

Displacement is the output of air by a compressor at zero pressure, or free air delivery.

1. WHAT IS AN AIR COMPRESSOR?

An air compressor is a machine designed to raise the pressure of air from normal atmospheric pressure to some higher pressure, as measured in pounds per square inch (psi). While normal atmospheric pressure is about 14.7 pounds per square inch, a compressor will typically deliver air at pressures up to 175 psi.

NOTICE

When selecting a compressor remember this rule of thumb. The cubic feet per minute delivered by an electrically powered 2 stage industrial air compressor is 4 times the motor's horse power rating. (CFM=4xHP)

2. WHAT TYPES OF COMPRESSORS ARE MOST COMMON IN SPRAY FINISHING OPERATIONS?

There are two common types; the piston-type design and the rotary screw design. Because most commercial spray finishing operations consume large quantities of compressed air at relatively high pressures, the piston type compressor is the more commonly used.

3. HOW DOES A PISTON TYPE COMPRESSOR WORK?

This design elevates air pressure through the action of a reciprocating piston. As the piston moves down, air is drawn in through an intake valve. As the piston travels upward, that air is compressed. Then, the now-compressed air is discharged through an exhaust valve into the air tank or regulator.

Piston type compressors are available with single or multiple cylinders in one or two-stage models, depending on the volume and pressure required.

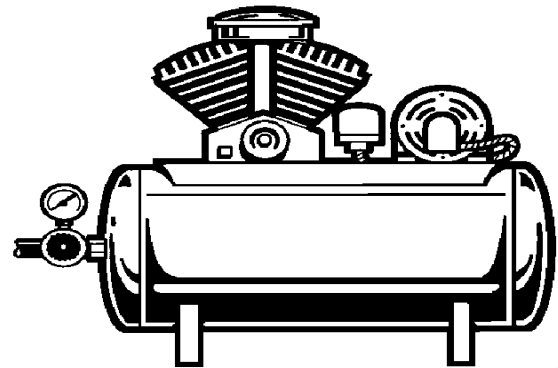


Figure 1: Piston Type Air Compressor

4. HOW DOES A ROTARY SCREW COMPRESSOR WORK?

Rotary screw compressors utilize two intermeshing helical rotors in a twin bore case. Air is compressed between one convex and one concave rotor. Trapped volume of air is decreased and the pressure is increased.

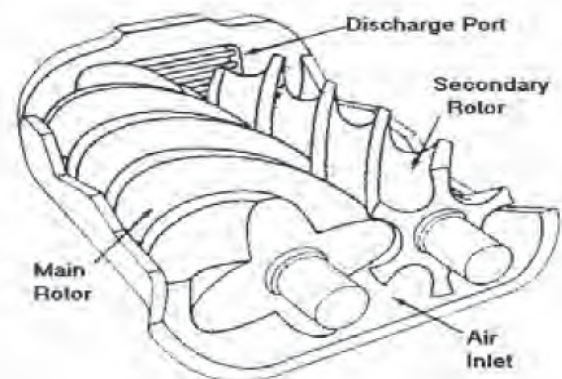


Figure 2: Rotary Type Screw Air Compressor

5. WHAT IS A SINGLE STAGE COMPRESSOR?

This is a piston-type compressor with one or more cylinders, in which air is drawn from the atmosphere and compressed to its final pressure with a single stroke. All pistons are the same size, and they can produce up to 125 psi.

6. WHERE ARE A SINGLE STAGE COMPRESSORS USED?

The application of this compressor is usually limited to a maximum pressure of 100 psi. It can be used above 100 psi, but above this pressure, two stage compressors are more efficient.

7. WHAT IS A TWO STAGE COMPRESSOR?

A compressor with two or more cylinders of unequal size in which air is compressed in two separate steps.

The first (the largest) cylinder compresses the air to an intermediate pressure. It then exhausts it into a connecting tube called an intercooler.

From there, the intermediate pressurized air enters the smaller cylinder, is compressed even more and is delivered to a storage tank or to the main air line.

Two stage compressors can deliver air to over 175 psi and are normally found in operations requiring compressed air of 125 psi or greater.

8. WHAT ARE THE BENEFITS OF TWO STAGE COMPRESSORS?

Two stage compressors are usually more efficient. They run cooler and deliver more air for the power consumed, particularly in the over 100 psi pressure range.

INTRODUCTION

Containing the overspray and keeping it out of the air and off other objects is an important consideration in a spray finishing operation.

This chapter looks at the primary method of controlling overspray in the spray booth. It discusses various types of booths and details periodic maintenance.

1. WHAT IS A SPRAY BOOTH?

A compartment, room or enclosure of fireproof construction; built to confine and exhaust overspray and fumes from the operator and finishing system.

There are various models available, designed for particular spray applications.

SAFETY

Consult the National Fire Protection Association (NFPA) pamphlet #33 and the O.S.H.A. requirements for construction specifications.

2. WHAT ARE THE BENEFITS OF A SPRAY BOOTH?

A well-designed and maintained spray booth provides important advantages:

- It separates the spraying operation from other shop activities, making the spraying, as well as the other operations, cleaner and safer.
- It reduces fire and health hazards by containing the overspray.
- It provides an area that contains residue, making it easier to keep clean. It also keeps both the operator and the object being sprayed cleaner.
- In a booth equipped with adequate and approved lighting, it provides better control of the finish quality.

3. WHAT TYPES OF SPRAY BOOTHS ARE THERE?

There are two; the dry filter type and the waterwash type.

4. WHAT IS A DRY FILTER TYPE SPRAY BOOTH?

This booth draws overspray contaminated air through replaceable filters and vents the filtered air to the outside.

It is the most common type of booth for most industrial applications.

It is used for spraying low-volume, slower-drying materials, and is not affected by color changes.

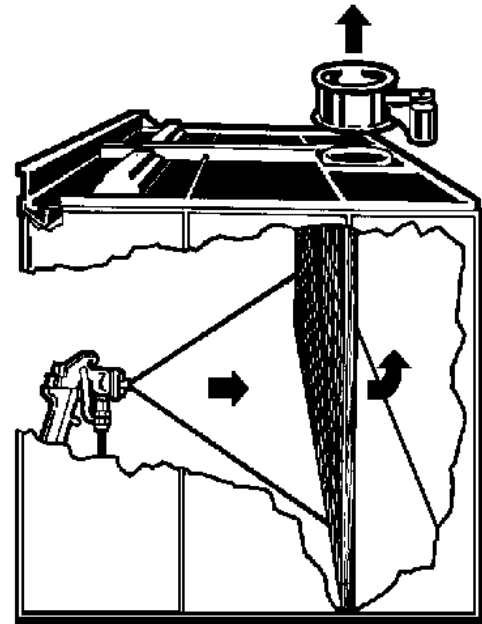


Figure 1: Dry Filter Type Spray Booth

5. WHAT IS A WATERWASH TYPE BOOTH?

A waterwash booth (see figure 2) actually washes the contaminated overspray air with a cascade of water, and traps the paint solids. Fewer paint particles reach the outside atmosphere to harm the environment.

Waterwash booths are generally used when spraying more than 15 gallons of material a day.

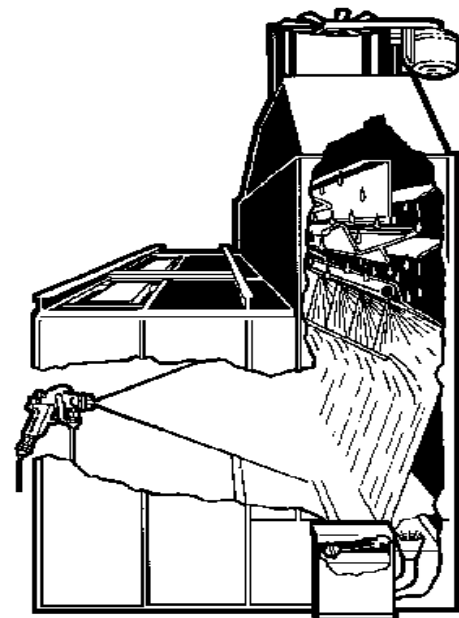


Figure 2: Waterwash Type Spray Booth

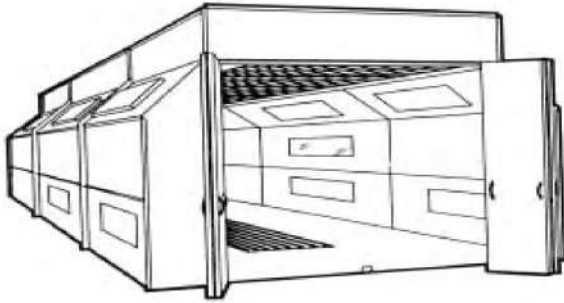


Figure 3: Automotive Downdraft Dry Filter Type Spray Booth

Too high a velocity wastes power and the energy required to heat make-up air.

9. WHAT IS A MANOMETER?

It is a draft gauge which indicates when paint arrestor filters or intake filters are overloaded.

NOTICE

Some states and local codes require a manometer gauge on each bank of filters to comply with OSHA regulations.

6. WHAT IS AN EXHAUST FAN?

A typical exhaust fan (see figure 4) consists of a motor, a multiple blade fan, pulleys and belts. It removes overspray from the spray booth area.

Contemporary exhaust fans are carefully designed to prevent overspray from coming into contact with the drive mechanism.

Blades are made of non-sparking metal, and they move the maximum volume of air-per-horsepower against resistance such as exhaust stacks, filters, etc. (See NFPA pamphlet #33.)

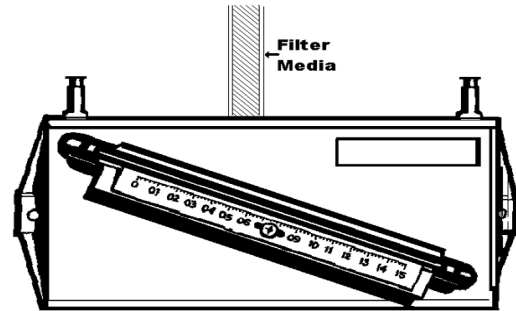


Figure 5: Manometer



Figure 4: Exhaust Fan

10. WHAT DOES AN AIR REPLACEMENT UNIT DO?

The volume of air exhausted from a spray booth is often equal to three or more complete air changes per hour.

Under such conditions, the temperature may become irregular and uncomfortable. Excessive dust may become a problem.

To prevent these conditions, sufficient "make-up" air must be introduced to compensate for the exhausted air.

The air replacement unit automatically supplies this "makeup" air - both filtered and heated - to eliminate the problems of air deficiency.

7. WHAT IS AIR VELOCITY?

Air velocity in a finishing operation is the term used to describe the speed of air moving through the empty spray booth.

8. WHAT EFFECT HAS AIR VELOCITY ON SPRAY BOOTH EFFICIENCY?

Air must move through the booth with sufficient velocity to carry away overspray.

Too low a velocity causes poor, even potentially dangerous working conditions, especially when the material contains toxic elements. It also increases maintenance costs.

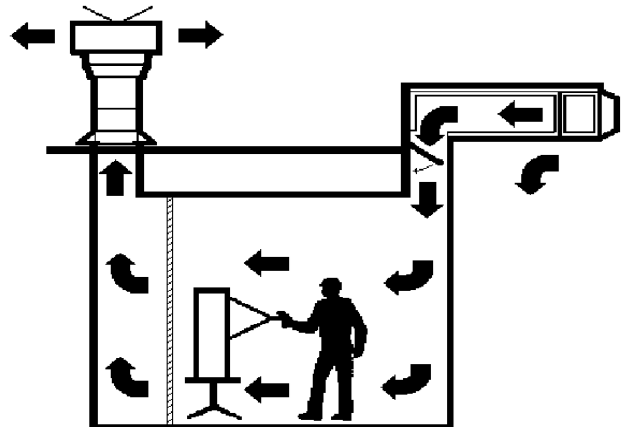


Figure 6: Air Replacement Unit

11. WHAT ROUTINE MAINTENANCE DOES A DRY TYPE SPRAY BOOTH REQUIRE?

- The continuous flow of air through the booth eventually loads the filters with dirt and overspray. Periodically, inspect and replace them with multistage filters, designed for spray booth use. Single-stage furnace filters will not do the job.
- Monitor the manometer readings daily, and know what a normal reading should be.
- Keep the booth free of dirt and overspray. Floors and walls should be wiped down after every job. Pick up scrap, newspapers, rags, etc.
- Coat the inside of the booth with a strippable, spray-on covering. When the overspray on it becomes too thick, strip and recoat.
- Periodically check the lighting inside the booth, and replace weak or burned out bulbs. Improper lighting can cause the operator to apply a poor finish.

12. WHAT ROUTINE MAINTENANCE DOES A WATERWASH TYPE BOOTH REQUIRE?

- Compounding of the water in this type unit is essential. Employ only booth treatment chemicals in accordance with suppliers' recommendations. The ph of the water should be between 8 and 9.
- Maintain the water level at the proper setting per manufacturers' specifications.
- Check the tank for paint buildup on the bottom, check the pump strainer to keep it clean and clear, check the air washer chamber and the nozzles in the header pipe. If the nozzles are plugged, the overspray will encroach on the wash baffle section, fan and stack.
- Periodically check the float valve for proper operation. Flood the sheet to be sure there is a uniform flow over the entire surface.
- Keep the booth interior and exhaust stack free from overspray and dirt accumulation.

13. WHAT CHECKS CAN BE USED TO ASSURE GOOD RESULTS FROM A SPRAY BOOTH?

- Keep the interior of the booth clean.
- Maintain and replace intake and exhaust filters when necessary.
- Caulk all seams and cracks where dirt might enter.
- Maintain and clean all equipment used in the booth.
- Keep operators clothing clean and lint-free.
- Perform routine maintenance above on a scheduled basis.

INTRODUCTION

Diaphragm pumps can serve several purposes in a spray system. They can be used as a transfer pump to move coatings from one container to another (ie. drum to a pressure pot).

In many cases larger diaphragm pumps can be used in a paint supply room to supply pressure to low pressure spray guns either in a dead-end system or a circulating system.

They may also be used in the spray booth to siphon directly out of a container supplying low pressure coatings to the spray gun. If required the coating could be returned to the source in a circulating system.



Figure 1: Wall Mount Gemini Two Pump

1. HOW ARE DIAPHRAGM PUMP PRESSURES DETERMINED?

Diaphragm pumps are normally a 1:1 ratio. The maximum pressure would be limited by the pump design (ie. 100 psi) or by the available pressure to the pump.

2. WHAT IS MEANT BY PRIMING THE PUMP?

Before setting working fluid pressures, start an empty pump by slowly opening the air pressure valve (or regulator) to the air motor. When the pump no longer cycles (full of coating), set the fluid pressure to the working pressure.

If the air motor receives full working pressure with an empty fluid section, the fluid section contains air and will initially run at high speed with no lubrication. This will increase the risk of damaging the fluid section.

3. HOW DOES A DIAPHRAGM PUMP WORK?

We will assume the pump in figure 2 is primed and the connecting rod at its maximum leftward movement and the pump is ready to move to the right. When fluid is called for, both diaphragms begin to move to the right via the rod connecting them. The four ball/seat valves behave as follows:

- Ball Check A Remains closed due to pressure in the right hand chamber.
- Ball Check B Opens to allow fluid in the right hand chamber to exit the pump.
- Ball Check C Remains closed due to pressure in the upper portion of the pump.
- Ball Check D Opens to allow fluid to be siphoned from the material container.

When the connecting rod causes both diaphragms to move to the left, the four ball check behave in a direction opposite to the above.

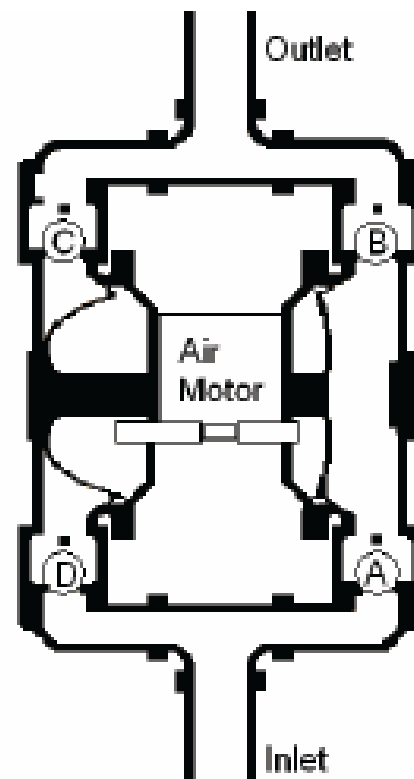


Figure 2: Diaphragm Pump Section View

HOW DO I TROUBLESHOOTING A DIAPHRAGM PUMP AIR MOTOR?

Problem	Cause	Correction
Freezing Air Motor	Air exhausting from the pump at higher cycle rates tends to freeze (stall) the motor.	Pipe exhaust away from pump. Reduce pump cycle rate (see pump service manual).
	High humidity and/or cycle rate.	
Dirt, Debris, Oil and/Or Water In Air Supply	Dirt can plug internal ports & shear air motor o-rings.	Install air filtration (clean/dry air). Check main air supply. Install proper filtration.
	Improper or excess lubrication can cause air motor o-rings to swell and stall the pump.	
	Water can wash out factory installed lubricant, leading to pump failure.	
Material Discharged From Air Exhaust When Idle	Diaphragm failure, or diaphragm plates loose.	Replace diaphragms, check for damage and ensure diaphragm plates are tight.
	Worn or damaged diaphragm.	Inspect and if need replace diaphragm. Check for excessive inlet pressure or air pressure. Consult Chemical Resistance Chart for compatibility with products, cleaners, temperature limitations and lubrication.
Pump Blows Air Out Main Air Exhaust When Idle	Pilot valve assembly stuck or damaged.	Check pilot valve assembly, valve plate and/or seals for wear and debris.
	Sleeve and "O" Ring damaged.	Check sleeve and "O" ring on diaphragm connecting rod.

⚠ DANGER

Aluminum pumps may violently react with materials containing HHC (Hologenated Hydrocarbon) solvents, ie. Carbon Tetrachloride.

HOW DO I TROUBLESHOOTING A DIAPHRAGM PUMP WET SECTION?

Problem	Cause	Correction
Leaking at Bolts	Old/worn/stretched bolts do not produce a tight seal.	Replace bolts. Check for lock tight or lock washers being used.
Stuck Open Ball Checks	Checks cannot seat properly. Fluid pressure will be reduced or eliminated.	Clean or replace ball check assembly.
Fluid Compatibility	Incompatibility can reduce life of pump.	Consult Chemical Resistance Chart for compatibility with products, cleaners, temperature limitations and lubrication.
Under Sizing	Pump cannot meet application requirements which leads to a shorter pump life. (Due to high cycle rates)	Consult pump specifications in manual.
Pump Will Not Prime Or Meet Delivery Requirements	Suction line blocked or undersized, clogged ball seats.	Clean or replace ball check assembly.
	Suction line too long.	Reduce pump suction line distance.
	Suction line pulling material too far above top of fluid level.	Check suction tube level in material.
Air Bubbles In Product Discharge	Introducing air from bad seal.	Check connections of suction plumbing.
		Check "O" rings between intake manifold and fluid caps.
Low Output Volume	Lack of supply air to pump.	Check air at main supply.
	Failed back pressure regulator or blockage.	Check back pressure regulator settings and plugged outlet hose.
	Pump mounted in vertical stroke position.	Change stroke position to horizontal.
	Cavitation occurs when material is exiting the pump faster than can be drawn in.	Check for pump cavitation - Suction pipe minimum 1/2" and non-collapsible.
	Loose connections or joints.	Check all intake & suction joints - Must be airtight. (Use Teflon tape or sealant if necessary.)
	Stuck or closed ball checks.	Check for sticking or improperly seating check valves.

INTRODUCTION

High pressure spray equipment will typically use between 300 and 4000 psi of fluid pressure. Low pressure equipment (air spray and HVLP) typically use 5-30 psi. When high volume applications and heavy film builds are called for, high pressure equipment excels.

Airless and air assist airless spray guns are used in high pressure finishing. Also required is a pump capable of delivering the pressures required for high pressure guns.

Other equipment concerns are hoses, regulators, filters, heaters and any other equipment that is subjected to the pressures being used and must be rated to handle the pressure.

1. WHAT ARE THE ADVANTAGES OF HIGH PRESSURE FINISHING?

- Speed of Application. (Due to the high flow rates, high pressure equipment will be considerably faster than low pressure equipment.)
- Improved Transfer Efficiency.
- Little or no air in the spray pattern.
- Sprays Most Coatings.
- Cost for high volume and high film build applications.

2. WHAT ARE THE DISADVANTAGES OF HIGH PRESSURE FINISHING?

- Safety issues must be addressed.
- More training is required.
- Limited equipment flexibility.
- Unlike low pressure equipment, cup guns, feathering the trigger and pattern adjustment are not available.
- Higher Initial Costs: high pressure equipment must be able to handle the higher pressures used. In addition, pumps are required to generate the pressures.
- Not For Small Quantities: high pressure equipment flow rates are generally rated in gallons per minute, low pressure equipment in ounces per minute.
- Plugging Tips: Due to the small opening in the fluid tip, plugging is not uncommon in high pressure equipment. Treatment and prevention for plugging may be found in the troubleshooting section of this manual.
- Heat may be required for high solids coatings: When using today's higher solid materials, heating of the material to lower the viscosity may be required to achieve the atomization required.
- Not For Fine Finish: The atomization capabilities of high pressure equipment will not allow it to obtain an automotive finish. Acceptability will depend on the finish standards of the product being sprayed as well as the characteristics of the coating.

SAFETY

3. WHAT ARE THE SAFETY CONCERNS WITH HIGH PRESSURE EQUIPMENT?

- Skin Injection: high pressure equipment has the capability of injecting coating into fingers, hands, etc.

SAFETY

Follow all safety instructions included with the equipment. Use tip guards and trigger locks where appropriate.

- Supporting Equipment: Insure that all supporting equipment is rated for the pressures that could be generated. Use the maximum pump pressure as a guide.

SAFETY

Respirators: Use the appropriate protection device as listed in the coating's Safety Data Sheet (SDS).

! WARNING

INJECTION HAZARD

Spray from the gun, hose leaks, or ruptured components can inject fluid into your body and cause extremely serious injury, including poisoning or the need for amputation.

Splashing fluid in eyes or on skin can also cause a serious injury.

Fluid injected into the skin might look like just a cut, but is a serious injury and should be treated as such.

**GET IMMEDIATE MEDICAL ATTENTION.
INFORM THE PHYSICIAN WHAT TYPE OF
MATERIAL WAS INJECTED.**

Do not point the spray gun at anyone or any part of the body.

Do not put fingers or hand over the spray tip.
Do not stop or detect fluid leaks with a rag, hand, body or glove.

Do not use a rag to blow back fluid.

THIS IS NOT AN AIR SPRAY GUN.

Be sure the trigger operates safely before spraying.
Engage the gun safety when not spraying.
**ALWAYS RELIEVE THE PRESSURE WHENEVER
WORKING ON THE SPRAY GUN.**

Tighten all fluid connections before operating equipment.

Check all hoses, tubes, and couplings daily. Replace all worn, damaged, or loose parts immediately.

AIRLESS AND AIR ASSIST AIRLESS GUNS

High pressure spraying requires the use of spray guns that can withstand the pressures associated with the pressures delivered via piston pumps.

Airless and Air Assisted Airless are currently available in both manual and automatic models.

Some models may have maximum pressures below the pressures the pumping system may deliver.

Consult your distributor to determine your pump.

1. WHAT IS AN AIRLESS GUN?

An airless gun uses high hydraulic pressure to force coating through a small elliptical shaped orifice to atomize.

2. WHAT DO I NEED TO KNOW TO CHOOSE AN AIRLESS FLUID TIP?

The following will determine pattern size and atomization:

- Fluid tip orifice shape
- Fluid tip orifice area
- Fluid viscosity
- Fluid pressure

Fluid tips for airless guns are sized based on an equivalent circular opening.

As an example, a .015" opening can take on many different shapes, thus different pattern sizes and atomization levels.

For example, Table 1 shows 7 different .015 fluid tips available for one model of an airless spray gun.

The shape of the opening is the variable that determines the pattern size.

NOTICE

The larger pattern sizes are the result of a tip opening that is more slender than the shorter pattern tip. This will give a larger pattern size at the expense of more frequent tip plugging and shorter tip life.

Table 1: Different .015 Fluid Tip Sizes		
Part Number	Size	Pattern Width
114-01506	.015	4" – 6"
114-01508	.015	6" – 8"
114-01510	.015	8" – 10"
114-01512	.015	10" – 12"
114-01514	.015	12" – 14"
114-01516	.015	14" – 16"
114-01518	.015	16" – 18"

3. HOW DOES AN AIRLESS GUN OPERATE?

An airless spray gun uses high hydraulic fluid pressure generated by a pump. The fluid is forced through a small elliptical shaped orifice (fluid tip or fluid nozzle) to generate the pattern.



Figure 1: Airless Spray Gun

4. WHAT IS AN AIR ASSIST AIRLESS GUN?

When air assist airless gun (see Figure 4) is set up with pressures under 2000 psi, the possibility of incomplete atomization increases. The net result is a pattern that has "tails" at the top and bottom. If sprayed with such a pattern, one would see a stripe at the top and bottom of each pass (see figure 2).




Figure 2: Incomplete Atomization

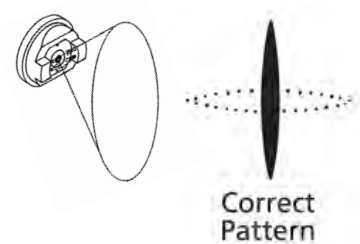


Figure 3: Air Assist

An air cap similar to a conventional or HVLP spray gun is added to a high pressure spray gun, thus the name Air Assist Airless. Set the pressure on the assist air is set high enough to eliminate the tails. (see figure 3)



Figure 4: Air Assist Gun

INTRODUCTION

A pump is required to generate the pressures required for airless and air assist airless spray guns.

The most common pump used to supply high pressure spray guns is an air driven two ball piston pump.



Figure 1: Two Ball Piston Pump

1. HOW ARE PISTON PUMP PRESSURES DETERMINED?

Pump ratios are determined by the size of the piston in the air motor compared to the size of the piston in the fluid section.

The maximum pump pressure available from a pump is the ratio of the pump multiplied by the maximum air inlet pressure as stated in the pump literature.

As an example, consider a piston pump with an 8" air motor and a 2" fluid section:

$$8" = 50.24 \text{ square inch area}$$

$$2" = 3.14 \text{ square inch area}$$

$$50.24/3.14 = 16:1 \text{ ratio}$$

If the pump had a maximum air inlet pressure of 100 psi, the maximum fluid pressure the pump could generate is 1600 psi.

2. WHAT RATIO DO I NEED FOR MY SPRAY GUN?

It is generally recommended that the maximum usable pressure is approximately 60-70% of the maximum pump pressure. A spray gun that requires 1000 psi of fluid pressure would need approximately an 18:1 pump (60% times 1800 psi would give 1080 psi of working pressure).

Other factors that influence ratio selection include:

- Gun distance from pump (pressure drop).
- Circulation requirements (if used).
- Viscosity of material.
- Size of fluid tip in gun.
- Pipe layout

3. WHAT IS MEANT BY PRIMING THE PUMP?

Before setting working fluid pressures, start an empty pump by slowly opening the air pressure valve (or regulator) to the air motor. When the pump no longer cycles (full of coating), adjust the regulator to set the fluid pressure to the working pressure.

If the air motor receives full working pressure with an empty fluid section, the fluid section contains air and will initially run at high speed with no lubrication. This will increase the risk of friction/heat damaging the packings and/or fluid section.

4. HOW DOES A TWO BALL FLUID SECTION WORK?

The fluid section is connected to the air motor. As the air motor moves up (1 stroke) it brings the displacement rod up. As the air motor moves down, it pushes the displacement rod down.

During the upstroke, the lower ball (B) raises allowing coating to enter the lower portion of the fluid section. Coating in the upper portion of the fluid section is pushed out of the outlet. The upper ball (A) remains closed. (see Figure 2)

During the downstroke, the lower ball remains closed. The upper ball is forced open allowing coating from the lower portion of the pump to enter the upper portion pushing coating out of the outlet.

If the pump is designed properly, 50 percent of the pumps output will be delivered on each stroke. (one upstroke, one downstroke). Note that with most 2 ball pumps all of the coating siphoned into the pump for the complete cycle enters the fluid section on the upstroke.


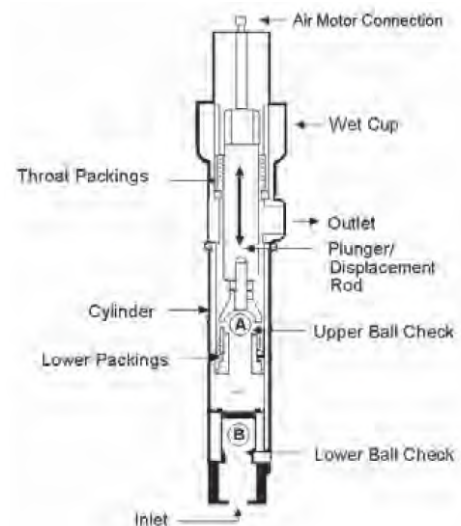


Figure 2: Two Ball Fluid Section

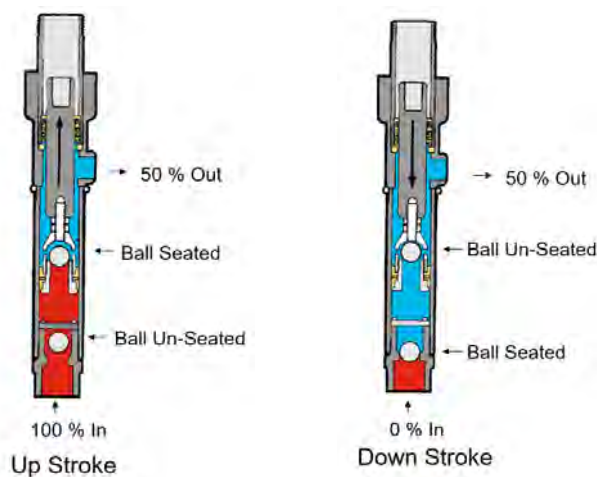

5. WHAT IS THE PURPOSE OF THE WET CUP?

Lubrication for the upper packings is provided by a lubricant added to the "Wet Cup" at the upper portion of the fluid section. This cup is not designed to contain solvent. Solvent will evaporate, leaving the upper packings without lubricant. Throat Seal Lubricant (TSL) should be used in the wet cup with the appropriate specification depending on water or solvent based materials being used.

6. WHAT IS MEANT BY CAVITATION?

A pump has little difficulty pushing material through the outlet into the piping or tubing system.

If the pump cannot bring material into the pump as fast as it pushes it out, a cavity or void is created in the input area. This could result if the material is highly viscous or the siphon tube is undersized or not airtight.

DEAD END SYSTEMS

Proper setup of high pressure equipment is necessary not only for efficient operation of the equipment, but safe operation as well.

Airless and Air Assist Airless may be supplied by a dead end system or a circulating system.

Following are instructions for a deadend system.

1. HOW DO I SETUP A SIMPLE (DEAD-END) HIGH PRESSURE SYSTEM?

Refer to Figure 3 for a typical "dead end" high pressure system.

1. 2 Ball Piston Pump Available in range of approximately 11:1 to 60:1
2. Filter/Regulator for Pump air motor. The air motor of a piston pump needs to be supplied with clean, dry air.
3. Surge tank (pulsation chamber) eliminates pulsation that happens when the piston changes direction.
4. Dual Fluid Filters prevents the line from being shut down when it is time to clean the filter.
5. Fluid pressure gauge monitors the fluid pressure in the main line.
6. Drop Line regulator allows for regulation to the required pressure of the spray gun.

2. WHAT PARAMETERS IN A DEAD-END SYSTEM SHOULD BE OF CONCERN?

- Use only components that can handle the pressures in the system. This includes all components in figure 3 as well as hoses, guns, fittings, etc.
- Fluid lines must be sized adequately to prevent large pressure losses.
- When using coating materials that "settle out" or high viscosity materials that need to be heated, a circulating system may be a better option.

3. HOW FAST OR SLOW SHOULD MY PUMP BE CYCLING?

Most pumps give a flow rate per cycle as well as a flow rate for 60 cycles. A flow rate of 15 cycles per minute will keep maintenance to a minimum. As you increase cycle speed, maintenance cost will increase as well.

If you undersize a pump, high cycle rates and high maintenance costs will be the result.

4. WHAT SAFETY ISSUES SHOULD BE ADDRESSED IN A HIGH PRESSURE SYSTEM?

- All components in the systems must be rated to handle the maximum pressure the pump could generate.
- Avoid the possibility of any portion of the body being near the fluid tip whenever there is a chance of fluid leaving the tip. If you inject your skin with coating, seek medical help immediately.
- If the gun is equipped with a trigger safety, engage it when the gun is not in use.
- If the gun is equipped with a tip guard (duck bill), do not remove it.

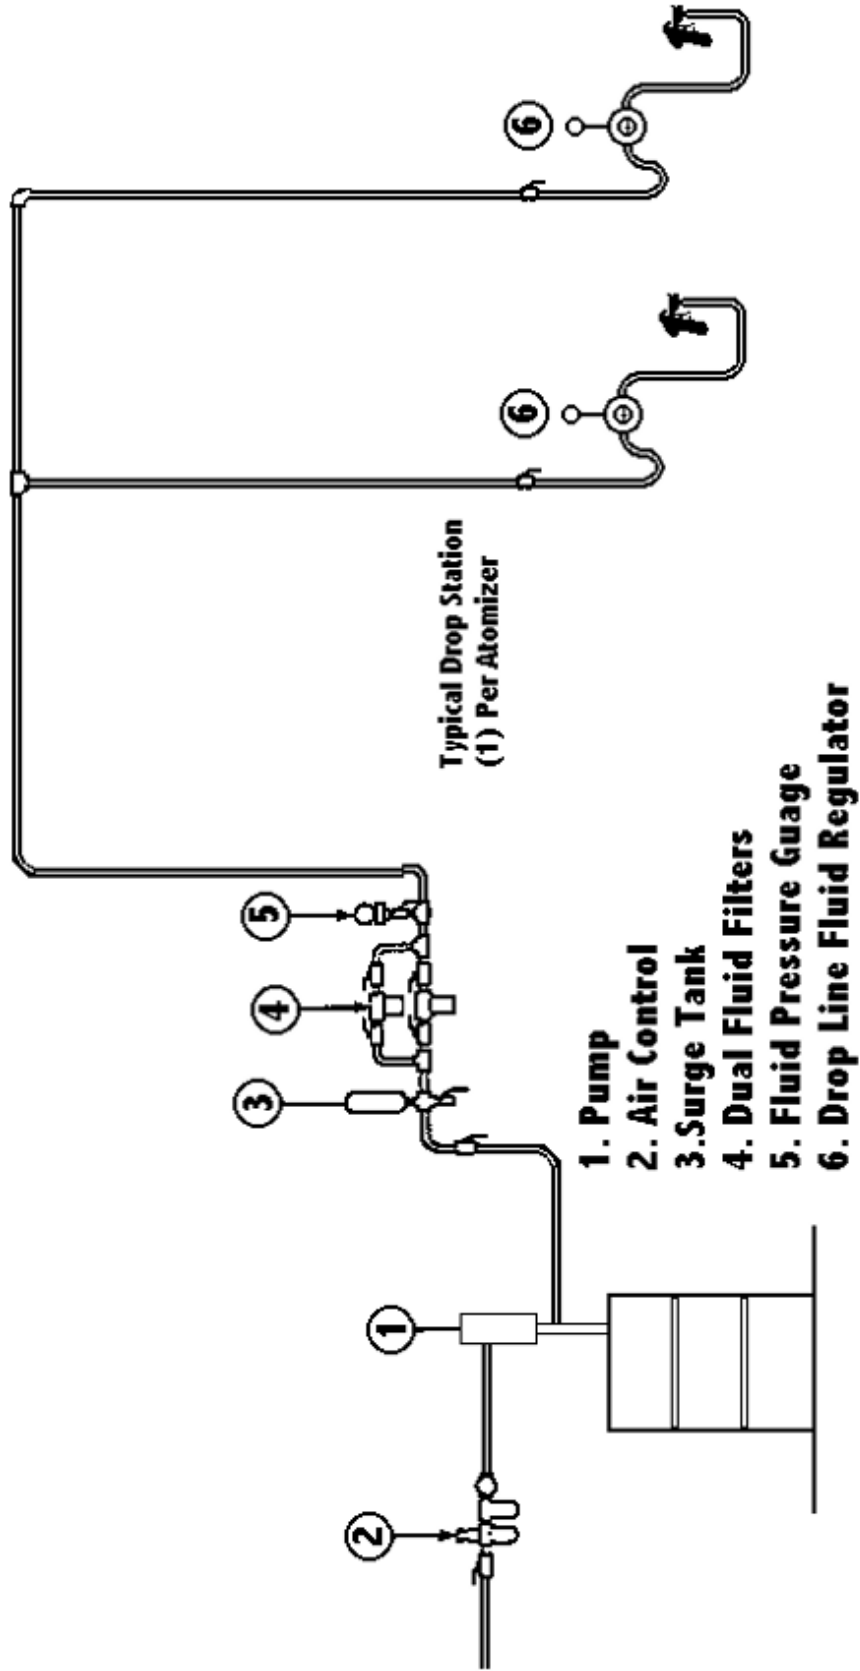


Figure 3: Dead End High Pressure System

TROUBLESHOOTING

Problems arising in a high pressure pumping system can range from something as simple as a plugged fluid tip to a runaway pump. Service literature that accompanies your equipment is highly recommended reading.

⚠ WARNING

At a minimum, lock the trigger before working on a high pressure airless fluid tip. If possible, remove the pressure to the gun.

⚠ DANGER

Before maintenance or repair of the high pressure system, be certain all pressure is completely vented from the pump, suction, discharge, piping, and all other openings and connections. Be sure the air supply is locked out or made non-operational, so that it cannot be started while work is being done on the system. Be certain that approved eye protection and protective clothing are worn all times in the vicinity of the pump. Failure to follow these recommendations may result in serious injury or death.

HOW DO I TROUBLESHOOTING A HIGH PRESSURE DEAD END SYSTEM?

	Problem	Cause	Correction
Gun	Plugged Airless Tips	Material builds up on orifice of tip.	Clean and/or replace tip orifice. Use only recommended tools to clean a plugged tip.
	Defective Spray Pattern	Airless: Worn out or dirty tip. Air Assist Airless: Worn out of dirty aircap and or fluid tip.	Airless: Replace or clean tip. Air Assist Airless: Rotate the air cap 180 degrees. If the pattern changes, clean or replace the air cap. If the pattern did not change, clean or replace the fluid tip.
Pump	Runaway Pump	When the material supply “runs out”, the pump will cycle at maximum speed.	Install a runaway detecting valve on the air line between the air motor and regulator to prevent damage to the pump.
Air Motor	Air Leakage Out Of Main Exhaust	Worn insert. Worn valve plate & pilot valve assy. Damaged piston assy.	Check all three parts and replace if worn.
Fluid Section	No Material At Outlet (Pump Continually Cycles)	Lack of supply material.	Check material supply.
	Material On One Stroke Only (Fast Down Stroke)	Lower ball not properly seating.	Check lower balls and replace if worn.
	Material On One Stroke Only (Fast Upstroke)	Worn or damaged seals.	Check seals and replace if worn.
	Material Leakage Form Solvent Cup	Worn or improperly adjusted upper packings.	Check packings and adjustment nut and tighten or replace if worn.
	Air Bubbles In Product Discharge	Siphon kit improperly installed (not air tight).	Check siphon kit for proper installation.

INTRODUCTION

A four ball pump generally is used in a “pump house” or “paint kitchen” for delivering lower pressures a long distance or high flow rates.

Pressures tend to be much lower than 2 ball pumps and are often regulated down at the point of use for air atomized spray guns.



Figure 1: Four Ball Piston Pump

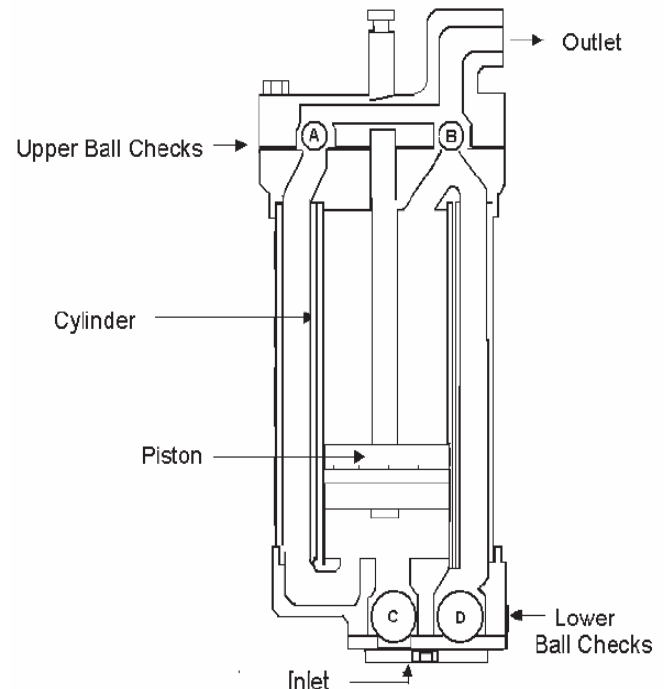


Figure 2: Four Ball Fluid Section

1. WHAT RATIOS ARE AVAILABLE IN A FOUR BALL PUMP?

Due to the larger fluid section, a very large air motor would be required to achieve the typical pressures achieved with two ball pumps. Using the same air motors used in two ball pumps, four ball pumps typically top out at a 25:1 ratio.

2. HOW DOES A FOUR BALL FLUID SECTION WORK?

A four ball piston pump fluid section contains four ball checks that alternate open and closed during its strokes (refer to figure 2).


During a pressure stroke, ball checks (D) and (A) open.

Ball (A) allows fluid to exit at pressure on one side of the pump, while ball (D) allows fluid to enter the pump to siphon fill.

Ball checks (B) and (C) remain closed to generate outlet fluid pressure.

During the change over, (D) and (A) close, while (C) and (B) open to allow fluid to exit at pressure on one side of the pump, while ball (C) allows fluid to enter the pump to siphon fill.

Ball checks (A) and (D) remain closed to generate outlet fluid pressure.

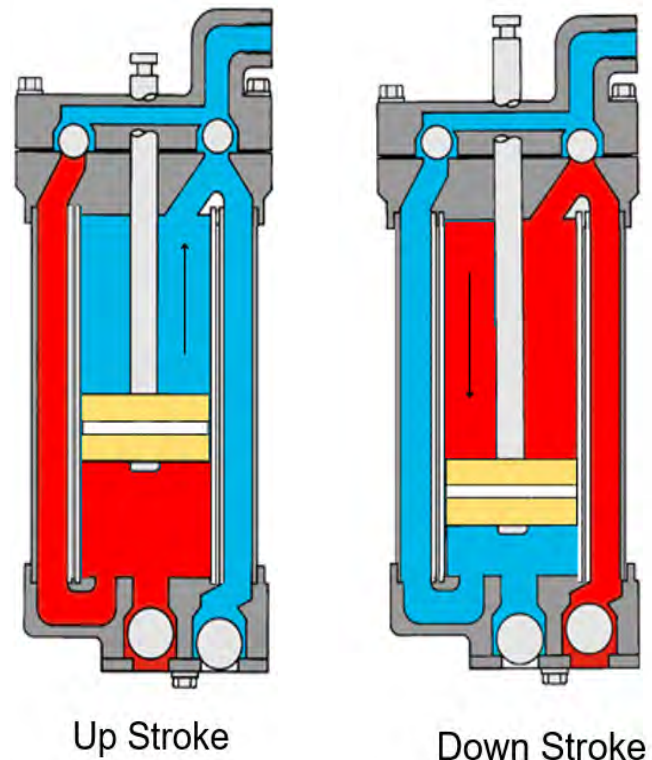

CIRCULATING SYSTEMS

A circulating system delivers fluid from the pump to the spray gun and back to the pump. (see figure 3).

You should consider a circulating system:

- When multiple stations need the same coating.
- When you want to put a paint heater in the system (to reduce viscosity without adding solvents).
- When you have problems with the solids of a coating “settling out”.

1. WHAT FLOW RATES ARE USED IN A CIRCULATING SYSTEM?

- Typical flow rates for solvent based materials are one foot per second (60 feet/min).
- Typical water based materials use one half foot per second (30 feet/min).
- Consult your Product Data Sheet or your coating supplier for recommendations for your coating.

2. HOW DOES A CIRCULATING SYSTEM WORK?

While some circulating systems can get very complex, refer to figure 3 for a very basic circulating system

The coating leaves the fluid section of the pump and travels through hoses, pipes, etc. to the spray gun.

A valve or tee at the spray drop line returns a portion of the material back to the pump on a return line.

The materials may return to the pump inlet or into the material container.

3. WHAT IS A BACK PRESSURE REGULATOR?

Referring to figure 3, imagine the back pressure regulator (3) removed from the system and the piping is straight through back to the pump.

There would be no reason for the material to flow to the spray gun as the path of least resistance for the material is back to the pump.

By putting a back pressure regulator in the system we create a dam that allows some fluid to return to source but set up a partial blockade (back pressure) to allow material to flow to the spray gun.

The general sequence for adjusting a back pressure regulator is:

1. Set the regulator to insure that the spray guns have adequate operating pressure.
2. Adjust for proper flow rate.
3. Adjust for proper pump speed.

4. WHAT OTHER COMPONENTS ARE USED IN A CIRCULATING SYSTEM?

- Downstream Fluid Regulators: For controlling pressure at each spray gun.
- Surge Tanks/Chambers: For suppressing the “wink” or pulse in the system, induced by the pump changing direction during the cycle.
- Heaters: For decreasing viscosity without adding solvent and maintaining a constant viscosity.
- Filters: For removing contaminants and preventing plugging gun fluid tips and spray defects.

NOTICE

Filters are located in the pressure side of the system.

- Strainers: For removing “trash” prior to entering the pump.

NOTICE

Strainers are located on the non-pressure portion of the system, normally on the end of the pump pick-up tube.

- Drum Lifts/Elevators: Allows the pump and drum lid to be raised to facilitate replacement of the drum.
- Agitator: Keeps material in suspension in the drum/ container.

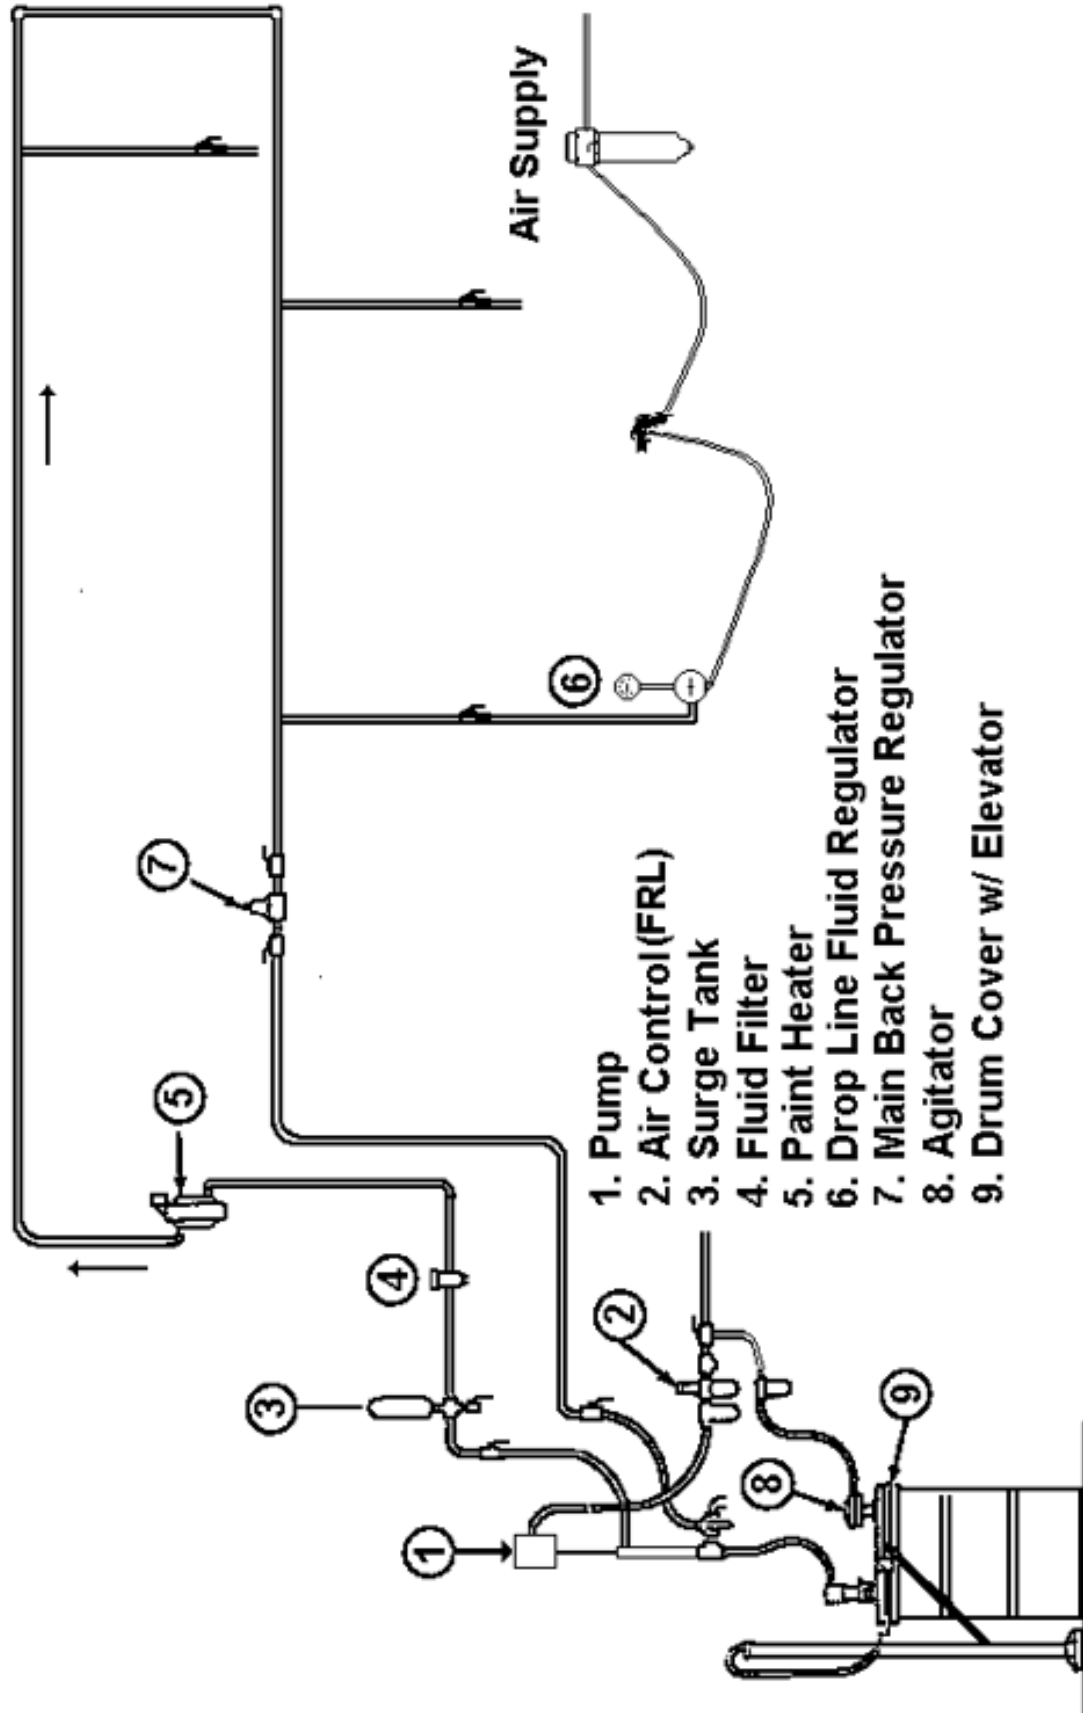


Figure 3: Circulating System

TROUBLESHOOTING

Problems arising in a low pressure pumping system can range from something as simple as a plugged fluid tip to a runaway pump. Service literature that accompanies your equipment is highly recommended reading.

⚠ WARNING

At a minimum, remove the pressure at the pump before performing maintenance.

⚠ WARNING

Before maintenance or repair of the circulation system, be certain all pressure is completely vented from the pump, suction, discharge, piping, and all other openings and connections. Be sure the air supply or power to the pump is locked out or made non-operational, so that it cannot be started while work is being done on the system. Be certain that approved eye protection and protective clothing are worn all times in the vicinity of the pump. Failure to follow these recommendations may result in serious injury or death.

HOW DO I TROUBLESHOOTING A LOW PRESSURE CIRCULATING SYSTEM?			
	Problem	Cause	Correction
Gun	See Chapter 5 "Air Atomizing Spray Guns" For Troubleshooting		
Material Supply	Air Bubbles	Low material level.	Add material.
	Low Flow	Suction point above paint line.	Install bottom outlet.
	Material Change	Agitator running to fast/slow.	Agitator speeds not set correctly.
Circulation Pump	Excessive Wear	Reference pump manual, Cycle rate limits.	Inspect and repair pump.
	Pressure/Volume Output Pulsation	Worn/damaged seals.	Check main power and main air supply.
	Pump Stalling	Dirty/stuck air controls.	Inspect and repair fluid lines, fluid filters, regulators and BPR.
	Over Pressure Faults	Material blockage.	
System Controls	Pump Won't Run Or Pump Settings Changed	PLC parameters restrict pump. Main air or power supply issues. BPR is closed.	Check set points/fault codes. Check power/main compressor. Check valves/regulators.
Circulation Lines	Low Material Volume	Circulation line restriction. Pipe ID under sized.	Inspect and/or repair circulation system.
	Viscosity/Material Changes	Circulation speed settings (suspension).	Inspect line distance and inspect speeds.
	Fluid Pressure Changes	BPR faulty and/or piping/system unbalanced.	Inspect the number of drops/locations from the supply to pump and/or to return.
Application Point	Low or No Material	Applicators and circulation lines.	Check power and main air source.
	Winking or Pulsing	Paint filters and regulators.	Verify gun operation.
	Air Being Observed	Material supply level.	Verify circulation speed and pressure settings.
	Pressure Fluctuations	Pump seals and ball checks.	Inspect for open suction connections.
Material Return	Finish Quality	Paint viscosity/material change.	Verify pump operation/material supply.
	Low or No Material	System in demand (guns triggered).	Inspect paint filters and regulators
	Air Being Observed	Paint supply low.	Inspect BPR and system operation.
	Inconsistent Return Flow	Air being introduced.	Verify system parameters and/or material supply.

PAINT AND SOLVENT SPECIFICATIONS

	Ransflex	NO.2 HANDGUN	TURBODISK™	AEROBELL® 33 AEROBELL® 168 AEROBELL® 268	RMA 600 Series
RECOMMENDED VISCOSITY USING A ZAHN NO. 2	18 TO 30 SEC	20 TO 60 SEC	20 TO 60 SEC	20 TO 60 SEC	20 TO 60 SEC
PAINT ELECTRICAL RESISTANCE**	.1 MΩ TO ∞	.1 TO 1 MΩ	.1 MΩ TO ∞	.1 MΩ TO ∞	.1 MΩ TO ∞
RECOMMENDED DELIVERY (UP TO)	1000 cc/min	180 cc/min	1000 cc/min	500 cc/min	1000 cc/min***

GUIDE TO USABLE SOLVENT SELECTION

Chemical Name	Common Name	Category	Flash Point†† (TCC)	*CAS No.	Evap. Rate†	Elec. Res.**
DICHLOROMETHANE	Methylene Chloride	Chlorinated Solvents	-	75-09-2	14.5	HIGH
VM & P NAPHTHA	Naphtha	Aliphatic Hydrocarbons	65°F	8030-30-6	10	HIGH
ACETONE	-	Ketones	-18°F	67-64-1	5.6	LOW
METHYL ACETATE	-	Esters	90°F	79-20-9	5.3	LOW
BENZENE	-	Aromatic Hydrocarbons	12°F	71-43-2	5.1	HIGH
ETHYL ACETATE	-	Esters	24°F	141-78-6	3.9	MEDIUM
2-BUTANONE	MEK	Ketones	16°F	78-93-3	3.8	MEDIUM
ISO-PROPYL ACETATE	-	Esters	35°F	108-21-4	3.4	LOW
ISOPROPYL ALCOHOL	IPA	Alcohols	53°F	67-63-0	2.5	LOW
2-PENTANONE	MPK	Ketones	104°F	107-87-9	2.5	MEDIUM
METHANOL	Methyl Alcohol	Alcohols	50°F	67-56-1	2.1	LOW
PROPYL ACETATE	n-Propyl Acetate	Esters	55°F	109-60-4	2.1	LOW
TOLUOL	Toluene	Aromatic Hydrocarbons	48°F	108-88-3	1.9	HIGH
METHYL ISOBUTYL KETONE	MIBK	Ketones	60°F	108-10-1	1.6	MEDIUM
ISOBUTYL ACETATE	-	Esters	69°F	110-19-0	1.5	LOW
ETHANOL	Ethyl Alcohol	Alcohols	-	64-17-5	1.4	LOW
BUTYL ACETATE	-	Esters	78°F	123-86-4	1.0	LOW
ETHYLBENZENE	-	Aromatic Hydrocarbons	64°F	100-41-4	.89	HIGH
1-PROPANOL	n-Propyl Alcohol	Alcohols	74°F	71-23-8	.86	LOW
2-BUTANOL	sec.-Butyl Alcohol	Alcohols	72°F	78-92-2	.81	LOW
XYLOL	Xylene	Aromatic Hydrocarbons	79°F	133-02-07	.80	HIGH
AMYL ACETATE	-	Esters	106°F	628-63-7	.67	MEDIUM
2-METHYLPROPANOL	iso-Butyl Alcohol	Alcohols	82°F	78-83-1	.62	LOW
METHYL AMYL ACETATE	-	Esters	96°F	108-84-9	.50	LOW
5-METHYL-2-HEXANONE	MIAK	Ketones	96°F	110-12-3	.50	MEDIUM
1-BUTANOL	n-Butyl Alcohol	Alcohols	95°F	71-36-3	.43	LOW
2-ETHOXYETHANOL	-	Glycol Ethers	164°F	110-80-5	.38	LOW
2-HEPTANONE	MAK	Ketones	102°F	110-43-0	.40	MEDIUM
CYCLOHEXANONE	-	Ketones	111°F	108-94-1	.29	MEDIUM
AROMATIC-100	SC#100	Aromatic Hydrocarbons	111°F	-	.20	HIGH
DIISOBUTYL KETONE	DIBK	Ketones	120°F	108-83-8	.19	MEDIUM
1-PENTANOL	Amyl Alcohol	Alcohols	-	71-41-0	.15	LOW
DIACETONE ALCOHOL	-	Ketones	133°F	123-42-2	.12	LOW
2-BUTOXYETHANOL	Butyl Cellosolve	Glycol Ethers	154°F	111-76-2		LOW
CYCLOHEXANOL	-	Alcohols	111°F	108-93-0	.05	LOW
AROMATIC-150	SC#150	Aromatic Hydrocarbons	149°F	-	.004	HIGH
AROMATIC-200	-	Aromatic Hydrocarbons	203°F	-	.003	HIGH

*CAS Number: Chemical Abstract Service Number.

**Electrical Resistance using the Ransburg Meter.

***See product manual for fluid rates per bell cup configurations.

†Information Obtained From: <http://solvdb.ncms.org>

††The lowest temperature at which a volatile fluid will ignite.

Evaporation Rate is Based Upon Butyl Acetate Having a Rate of 1.0

VISCOSITY CONVERSION CHART

Poise	Centipoise	Parlin 7	Parlin 10	Fisher 1	Fisher 2	Ford Cup 3	Ford Cup 4	Gardner-Holdt Bubble	Lithographic	Krebs UnitKU	Saybolt Universal SSU	Zahn 1	Zahn 2	Zahn 3	Zahn 4	Zahn 5	Sears Craftsman Cup	Din Cup 4
.1	10	27	11	20	-	-	5	A-4	-	-	60	30	16	-	-	-	-	10
.15	15	30	12	25	-	-	8	A-3	-	-	80	34	17	-	-	-	-	11
.2	20	32	13	30	15	12	10	-	-	-	100	37	18	-	-	-	-	12
.25	25	37	14	35	17	15	12	A-2	-	-	130	41	19	-	-	-	-	13
.3	30	43	15	39	18	19	14	A-1	-	-	160	44	20	-	-	-	-	14
.4	40	50	16	50	21	25	18	A	-	-	210	52	22	-	-	-	19	15
.5	50	57	17	-	24	29	22	-	-	30	260	60	24	-	-	-	20	16
.6	60	64	18	-	29	33	25	B	-	33	320	68	27	-	-	-	21	18
.7	70	-	20	-	33	36	28	-	-	35	370	-	30	-	-	-	23	21
.8	80	-	22	-	39	41	31	C	-	37	430	-	34	-	-	-	24	23
.9	90	-	23	-	44	45	32	-	-	38	480	-	37	10	-	-	26	25
1.0	100	-	25	-	50	50	34	D	-	40	530	-	41	12	10	-	27	27
1.2	120	-	30	-	62	58	41	E	-	43	580	-	49	14	11	-	31	31
1.4	140	-	32	-	-	66	45	F	-	46	690	-	58	16	13	-	34	34
1.6	160	-	37	-	-	-	50	G	-	48	790	-	66	18	14	-	38	38
1.8	180	-	41	-	-	-	54	-	000	50	900	-	74	20	16	-	40	43
2.0	200	-	45	-	-	-	58	H	-	52	1000	-	82	23	17	10	44	46
2.2	220	-	-	-	-	-	62	I	-	54	1100	-	-	25	18	11	-	51
2.4	240	-	-	-	-	-	65	J	-	56	1200	-	-	27	20	12	-	55
2.6	260	-	-	-	-	-	68	-	-	58	1280	-	-	30	21	13	-	58
2.8	280	-	-	-	-	-	70	K	-	59	1380	-	-	32	22	14	-	63
3.0	300	-	-	-	-	-	74	L	-	60	1475	-	-	34	24	15	-	68
3.2	320	-	-	-	-	-	-	M	-	-	1530	-	-	36	25	16	-	72
3.4	340	-	-	-	-	-	-	N	-	-	1630	-	-	39	26	17	-	76
3.6	360	-	-	-	-	-	-	O	-	62	1730	-	-	41	28	18	-	82
3.8	380	-	-	-	-	-	-	-	-	-	1850	-	-	43	29	19	-	86
4.0	400	-	-	-	-	-	-	P	-	64	1950	-	-	46	30	20	-	90
4.2	420	-	-	-	-	-	-	-	-	-	2050	-	-	48	32	21	-	95
4.4	440	-	-	-	-	-	-	Q	-	-	2160	-	-	50	33	22	-	100
4.6	460	-	-	-	-	-	-	R	-	66	2270	-	-	52	34	23	-	104
4.8	480	-	-	-	-	-	-	-	00	67	2380	-	-	54	36	24	-	109
5.0	500	-	-	-	-	-	-	S	-	68	2480	-	-	57	37	25	-	112
5.5	550	-	-	-	-	-	-	T	-	69	2660	-	-	63	40	27	-	124
6.0	600	-	-	-	-	-	-	U	-	71	2900	-	-	68	44	30	-	135
7.0	700	-	-	-	-	-	-	-	-	74	3375	-	-	-	51	35	-	160
8.0	800	-	-	-	-	-	-	-	0	77	3380	-	-	-	58	40	-	172

VISCOSITY CONVERSION CHART (cont.)

Poise	Centipoise	Parlin 7	Parlin 10	Fisher 1	Fisher 2	Ford Cup 3	Ford Cup 4	Gardner-Holdt Bubble	Lithographic	Krebs UnitKU	Saybolt Universal SSU	Zahn 1	Zahn 2	Zahn 3	Zahn 4	Zahn 5	Sears Craftsman Cup	Din Cup 4
9.0	900	-	-	-	-	-	-	V	-	81	4300	-	-	-	64	45	-	195
10.0	1000	-	-	-	-	-	-	W	-	85	4600	-	-	-	-	49	-	218
11.0	1100	-	-	-	-	-	-	-	-	88	5200	-	-	-	-	55	-	-
12.0	1200	-	-	-	-	-	-	-	-	92	5620	-	-	-	-	59	-	-
13.0	1300	-	-	-	-	-	-	X	-	95	6100	-	-	-	-	64	-	-
14.0	1400	-	-	-	-	-	-	-	1	96	6480	-	-	-	-	-	-	-
15.0	1500	-	-	-	-	-	-	-	-	98	7000	-	-	-	-	-	-	-
16.0	1600	-	-	-	-	-	-	-	-	100	7500	-	-	-	-	-	-	-
17.0	1700	-	-	-	-	-	-	-	-	101	8000	-	-	-	-	-	-	-
18.0	1800	-	-	-	-	-	-	Y	-	-	8500	-	-	-	-	-	-	-
19.0	1900	-	-	-	-	-	-	-	-	-	9000	-	-	-	-	-	-	-
20.0	2000	-	-	-	-	-	-	-	-	103	9400	-	-	-	-	-	-	-
21.0	2100	-	-	-	-	-	-	-	-	-	9850	-	-	-	-	-	-	-
22.0	2200	-	-	-	-	-	-	-	-	-	10300	-	-	-	-	-	-	-
23.0	2300	-	-	-	-	-	-	Z	2	105	10750	-	-	-	-	-	-	-
24.0	2400	-	-	-	-	-	-	-	-	109	11200	-	-	-	-	-	-	-
25.0	2500	-	-	-	-	-	-	Z-1	-	114	11600	-	-	-	-	-	-	-
30.0	3000	-	-	-	-	-	-	-	-	121	14500	-	-	-	-	-	-	-
35.0	3500	-	-	-	-	-	-	Z-2	3	129	16500	-	-	-	-	-	-	-
40.0	4000	-	-	-	-	-	-	-	-	133	18500	-	-	-	-	-	-	-
45.0	4500	-	-	-	-	-	-	Z-3	-	136	21000	-	-	-	-	-	-	-
50.0	5000	-	-	-	-	-	-	-	-	-	23500	-	-	-	-	-	-	-
55.0	5500	-	-	-	-	-	-	-	-	-	26000	-	-	-	-	-	-	-
60.0	6000	-	-	-	-	-	-	Z-4	4	-	2800	-	-	-	-	-	-	-
65.0	6500	-	-	-	-	-	-	-	-	-	30000	-	-	-	-	-	-	-
70.0	7000	-	-	-	-	-	-	-	-	-	32500	-	-	-	-	-	-	-
75.0	7500	-	-	-	-	-	-	-	-	-	35000	-	-	-	-	-	-	-
80.0	8000	-	-	-	-	-	-	-	-	-	37000	-	-	-	-	-	-	-
85.0	8500	-	-	-	-	-	-	-	-	-	39500	-	-	-	-	-	-	-
90.0	9000	-	-	-	-	-	-	-	-	-	41000	-	-	-	-	-	-	-
95.0	9500	-	-	-	-	-	-	-	-	-	43000	-	-	-	-	-	-	-
100.0	10000	-	-	-	-	-	-	Z-5	5	-	46500	-	-	-	-	-	-	-
110.0	11000	-	-	-	-	-	-	-	-	-	51000	-	-	-	-	-	-	-
120.0	12000	-	-	-	-	-	-	-	-	-	55005	-	-	-	-	-	-	-
130.0	13000	-	-	-	-	-	-	-	-	-	60000	-	-	-	-	-	-	-
140.0	14000	-	-	-	-	-	-	-	-	-	65000	-	-	-	-	-	-	-

VISCOSITY CONVERSION CHART (cont.)

Poise	Centipoise	Parlin 7	Parlin 10	Fisher 1	Fisher 2	Ford Cup 3	Ford Cup 4	Gardner-Holdt Bubble	Lithographic	Krebs UnitKU	Saybolt Universal SSU	Zahn 1	Zahn 2	Zahn 3	Zahn 4	Zahn 5	Sears Craftsman Cup	Din Cup 4
150.0	15000	-	-	-	-	-	-	Z-6	-	-	67500	-	-	-	-	-	-	-
160.0	16000	-	-	-	-	-	-	-	-	-	74000	-	-	-	-	-	-	-
170.0	17000	-	-	-	-	-	-	-	-	-	83500	-	-	-	-	-	-	-
180.0	18000	-	-	-	-	-	-	-	-	-	83500	-	-	-	-	-	-	-
190.0	19000	-	-	-	-	-	-	-	-	-	88000	-	-	-	-	-	-	-
200.0	20000	-	-	-	-	-	-	-	-	-	93000	-	-	-	-	-	-	-
300.0	30000	-	-	-	-	-	-	-	-	-	140000	-	-	-	-	-	-	-

Note: All viscosity comparisons are as accurate as possible with existing information. Comparisons are made with a material having a specific gravity of 1.0.

VOLUMETRIC CONTENT OF HOSE OR TUBE (English units)

I.D. (inches)	cc/ft.	Cross Section (sq. in.)	Length				
			5 ft. (60")	10 ft. (120")	15 ft. (180")	25 ft. (300")	50 ft. (600")
1/8	2.4	.012	.003 gal. .4 fl. oz.	.006 gal. .8 fl. oz.	.010 gal. 1.2 fl. oz.	.016 gal. 2.0 fl. oz.	.03 gal. 4.0 fl. oz.
3/16	5.4	.028	.007 gal. .9 fl. oz.	.014 gal. 1.8 fl. oz.	.022 gal. 2.7 fl. oz.	.036 gal. 4.5 fl. oz.	.072 gal. 9.0 fl. oz.
1/4	9.7	.049	.013 gal. 1.6 fl. oz.	.025 gal. 3.2 fl. oz.	.038 gal. 4.8 fl. oz.	.064 gal. 8.0 fl. oz.	.127 gal. 16.0 fl. oz.
5/16	15.1	.077	.020 gal. 2.5 fl. oz.	.040 gal. 5.1 fl. oz.	.060 gal. 7.6 fl. oz.	.100 gal. 12.7 fl. oz.	.199 gal. 25.5 fl. oz.
3/8	21.7	.110	.029 gal. 3.7 fl. oz.	.057 gal. 7.3 fl. oz.	.086 gal. 11.0 fl. oz.	.143 gal. 18.4 fl. oz.	.287 gal. 36.7 fl. oz.
1/2	38.6	.196	.051 gal. 6.5 fl. oz.	.102 gal. 13.1 fl. oz.	.153 gal. 19.6 fl. oz.	.255 gal. 3.6 fl. oz.	.510 gal. 65.3 fl. oz.

VOLUMETRIC CONTENT OF HOSE OR TUBE (Metric units)

I.D. (mm)	cc/m	Cross Section (mm ²)	Length				
			1.5 m	3.0 m	4.5 m	6.0 m	7.5 m
3.6	102	10.2	15.3 cc	30.5 cc	45.8 cc	61.1 cc	76.3 cc
5.6	246	24.6	36.9 cc	73.9 cc	110.8 cc	147.8 cc	184.7 cc
6.8	363	36.3	54.4 cc	109.0 cc	163.4 cc	217.9 cc	272.4 cc
8.8	608	60.8	91.2 cc	182.5 cc	273.7 cc	364.9 cc	456.2 cc

MANUAL CHANGE SUMMARY

Date	Description	Version
02/2025	Updated to new template, rebranded to Binks, added electrostatic powder application, additional electrostatic applicator pictures, transfer efficiency chart, threaded styles for pipe, circulating system troubleshooting and appendix information.	R2

NOTES

For technical assistance or to locate an authorized distributor, contact one of our international sales and customer support locations listed below.

REGION	BINKS CONTACT
Americas	Tel: 1-800-992-4657
Europe, Africa, Middle East	Tel: +4401202571111
India	marketingroa@binks.com
China	Tel: +862133730108
Korea	Tel: +82313663303
Japan	Tel: +81457856421
Australia	Tel: +61085257555

Binks®

Binks is a global leader in innovative finishing technologies.
Binks reserves the right to modify equipment specifications without prior notice.
Binks®, DeVilbiss® and Ransburg® are registered trademarks of Binks US, LLC.